



ELSEVIER

Contents lists available at ScienceDirect

Comptes Rendus Chimie

www.sciencedirect.com



Full paper/Mémoire

Host (nanocavity of zeolite-Y)–guest (molybdophosphoric acid) nanocomposite materials: An efficient catalyst for solvent-free synthesis and deprotection of 1,1-diacetates

Maryam Moosavifar^{a,*}, Shahram Tangestaninejad^b, Majid Moghadam^b,
Valiollah Mirkhani^b, Iraj Mohammadpoor-Baltork^b

^a Department of Chemistry, Faculty of Science, University of Maragheh, 55181-83111 Maragheh, Iran

^b Department of Chemistry, Catalysis Division, University of Isfahan, 81746-73441 Isfahan, Iran

ARTICLE INFO

Article history:

Received 23 January 2011

Accepted after revision 16 March 2011

Available online 12 May 2011

Keywords:

MPA-DAZY

Protection

Deprotection

1,1-diacetates

Solvent-free

ABSTRACT

In the present work, a mild and efficient method has been developed for the synthesis of acylals from aldehydes with acetic anhydride in the presence of molybdophosphoric acid encapsulated into dealuminated zeolite Y (MPA-DAZY) as a catalyst under solvent-free conditions at 45–55 °C in good to excellent yield. The deprotection of acylals has also been attained using this catalyst in acetonitrile. The catalyst was reused several times without efficient loss of its catalytic activity.

© 2011 Published by Elsevier Masson SAS on behalf of Académie des sciences.

1. Introduction

Protection of functional groups plays an important role in multi-step synthesis of natural products. However, selective protection and deprotection of carbonyl groups are substantial steps in synthetic organic chemistry [1]. Acylals (1,1-diacetates) are appropriate candidates to this aim due to their stability in basic and neutral reaction media as well as in aqueous acids [2]. Meanwhile, gem-diacetates derived from α,β -unsaturated aldehydes are useful as dienes for Diels–Alder cycloaddition reactions. Moreover, acylals are used as cross linking reagents for cellulose in cotton [3].

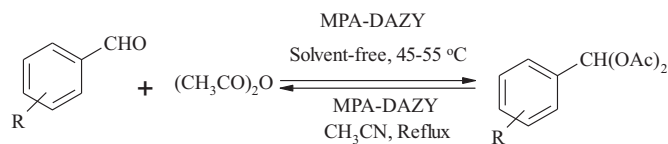
Several methods have been used for the synthesis of 1,1-diacetates from strong acids including sulfuric acid [4], methane sulfuric acid [5], sulfamic acid [6], Lewis acids as lithium bromide [7], aluminum chloride [8], anhydrous

ferrous sulfate [9], PCl_3 [10], FeCl_3 [11], NBS [12], Nafion-H [13], sulfated zirconia [14], montmorillonite clay [15], expansive graphite [16], aluminum dodecatungstophosphate [17], Well–Dawson acid ($\text{H}_6\text{P}_2\text{W}_{18}\text{O}_{62} \cdot 24\text{H}_2\text{O}$) [18] zeolite HSZ-360 [19], $\text{Cu}(\text{OTf})_2$ [20], $\text{Sc}(\text{OTf})_3$ [21], $\text{Bi}(\text{OTf})_3$ [22], $\text{Zn}(\text{BF}_4)_2$ [23], $\text{Bi}(\text{NO}_3)_3 \cdot 5\text{H}_2\text{O}$ [24] and ZrCl_4 [25] which are also efficient for this conversion. However, many of these methodologies have drawbacks, and involve strongly acidic conditions, corrosive reagents, long reaction times, high temperature and high toxicity. Recently, solvent-free reactions were developed because of their ecological and low-cost advantages. Some of these catalysts are $\text{P}_2\text{O}_5/\text{Al}_2\text{O}_3$ [26], dodecamolybdophosphoric acid [27], $\text{SO}_4^{2-}/\text{SnO}_2$ [28], bromodimethylsulfonium bromide [29], solid lithium perchlorate [30], [bmim] BF_4 [31], [Hmim] HSO_4 [32] zirconium sulfophenyl phosphonate [19] and Zeolite Y [33].

In this article, we report a new and efficient method for solvent-free conversion of aromatic aldehydes to their corresponding 1,1-diacetates with acetic anhydride and their deprotection in acetonitrile using encapsulated molybdophosphoric acid in dealuminated Y zeolite (MPA-DAZY) as a reusable catalyst (Scheme 1).

* Corresponding author.

E-mail addresses: m.moosavifar@maragheh.ac.ir, maryam_moosavifar@yahoo.com (M. Moosavifar).



Scheme 1. Synthesis of 1,1-diacetates under solvent-free conditions and their deprotection in acetonitrile using encapsulated molybdophosphoric acid in dealuminated Y zeolite (MPA-DAZY).

2. Experimental

All solvents and reagents were of the commercial reagent grade and obtained from Merck or Fluka. All of reaction mixtures were monitored by TLC. Melting points were recorded on a Barnstead Electrothermal 9200 apparatus, and are uncorrected. The NaY-zeolite was purchased from Sigma-Aldrich Chemical Company. The framework of NaY-zeolite contains aluminum atoms are basic and therefore, increase the decomposition of MPAs, or disturb the formation of MPA into the supercages of zeolite. Therefore, the modified DAZY (dealuminated zeolite Y) as support, was prepared by hydrothermal treatment [34]. Dealumination of NaY zeolite not only improves the zeolite stability but also yields a secondary pore system in zeolite matrix for deposition of the large MPA species [35]. Therefore, zeolite Y was dealuminated. The method reported by Mukai was used for the synthesis of $H_3PMo_{12}O_{40}$ encapsulated into dealuminated zeolite (MPA-DAZY) [36,37]. All products were known compounds and identified by comparing their physical data by their authentic samples.

2.1. General procedure for the preparation of 1,1-diacetates

In a round bottom flask equipped with a magnetic stirrer, aldehyde (1 mmol), acetic anhydride (3 mmol) and catalyst (250 mg, 0.01 mmol) were mixed and stirred at 45–55 °C for an appropriate time. The progress of the reaction was monitored by TLC (ethyl acetate/*n*-hexane 7:1). After the reaction was completed, saturated $NaHCO_3$ (5 ml) was added and the catalyst was filtered. The product was extracted with diethyl ether (2×15 ml) and the etherates were dried over Na_2SO_4 . The solvent was evaporated to give the corresponding 1,1-diacetate.

2.2. Catalyst recovery and reuse

The reusability of catalyst also was investigated in the multiple sequential reaction of 3-nitrobenzaldehyde as a model substrate. At the end of each reaction, the catalyst was filtered, activated by washing with ethyl acetate and drying at 120 °C for 3 h, and reused with fresh aldehyde and acetic anhydride.

2.3. General procedure for the deprotection of 1,1-diacetates

In a typical procedure, 1,1-diacetates (1 mmol) in acetonitrile (3 ml) and MPA-DAZY (500 mg, 0.02 mmol) were mixed and refluxed for an appropriate time. The progress of reaction was monitored by TLC (ethyl acetate/*n*-hexane 7:1). After completion of the reaction, the reaction mixture was diluted with ethyl acetate and

filtered. The organic layer was washed with $NaHCO_3$ (10%, 2×5 ml) and dried over Na_2SO_4 . The organic solvent was evaporated to produce the crude aldehyde. The residue was purified by plate chromatography (*n*-hexane/ether 4:1) to give the corresponding aldehyde.

3. Results and discussion

3.1. Catalytic performance in the protection of aldehydes

The MPA-DAZY catalyst was synthesized and characterized by infrared spectroscopy (FT-IR), X-ray diffraction (XRD), differential thermal gravimetry (DTG) and atomic absorption spectroscopic (AAS) techniques. The content of MPA in the synthesized sample, obtained by dissolving a small amount of the washed catalyst in hydrofluoric acid and hot concentrated hydrochloric acid, was determined by atomic absorption spectroscopy (AAS) [37].

The results showed that the catalyst loading was about 0.043 mmol/g of encapsulated catalyst. The reaction of aldehydes with acetic anhydride in the presence of MPA-DAZY produces the corresponding 1,1-diacetates (Scheme 1). First, the amount of catalyst was optimized in the reaction of 3-nitrobenzaldehyde with acetic anhydride. The results showed that highest yield was obtained with 250 mg (0.01 mmol) of catalyst (Table 1). For optimization of the reaction media, the same reaction was performed in

Table 1
Optimization of the catalyst amount in the reaction of 3-nitrobenzaldehyde with acetic anhydride under solvent-free conditions after 1 h.^a

Entry	Catalyst amount (mg)	Yield ^b (%)
1	100	40
2	150	65
3	200	84
4	250 (0.01 mmol of MPA)	95

^a Reaction conditions: 3-nitrobenzaldehyde (1 mmol), acetic anhydride (3 mmol).

^b Isolated yield.



















Table 2
The effect of solvent on the protection of 3-nitrobenzaldehyde with acetic anhydride catalyzed by MPA-DAZY after 1 h.^a

Entry	Solvent	Yield ^b (%)
1	CH_3CN	44
2	CH_3COCH_3	35
3	CH_3OH	40
4	CH_2Cl_2	25
5	Solvent-free	95

^a Reaction conditions: 3-nitrobenzaldehyde (1 mmol), acetic anhydride (3 mmol), catalyst (250 mg, 0.01 mmol).

^b Isolated yield.

Table 3
 Synthesis of 1,1-diacetates with anhydride acetic catalyzed by MPA-DAZY under solvent-free conditions and their deprotection in acetonitrile.^a

Entry	Substrate	Product	Yield ^b (%)	Protection		Deprotection	
				Time (min)	Reported	Yield ^b (%)	Time (h)
1			80	90	52–53 [19]	45	4
2			98	70	64–65 [26]	75	4
3			98	75	103 [38]	75	4
4			95	60	65–66 [39]	90	4
5			95	85	127 [26]	60	4
6			92	110	81–82 [26]	76	4
7			90	70	82–83 [39]	40	4
8			98	75	70–71 [40]	70	4
9			85	85	82–83 [41]	80	4

^a Reaction conditions: aldehyde (1 mmol), Ac₂O (3 mmol) catalyst (250 mg, 0.01 mmol).

^b Isolated yield.

Table 4

The results obtained in the reusability of MPA-DAZY and the amount of molybdenum leached in the reaction of 3-nitrobenzaldehyde with Ac_2O under solvent-free conditions after 1 h.^a

Run	Yield ^b (%)	Mo leached ^c (%)
1	95	3
2	87	4
3	80	5
4	76	1

^a Reaction condition: 3-nitrobenzaldehyde (1 mmol), acetic anhydride (3 mmol).

^b Isolated yield.

^c Determined by atomic absorption spectroscopy.

different solvents and also under solvent-free conditions. When the reaction was performed in solvent, the progress of the reaction was lower in comparison with solvent-free conditions. Therefore, the solvent-free conditions was used for the conversion of aldehydes to their corresponding 1,1-diacetates (Table 2). The amount of acetic anhydride was also optimized and the best result was obtained with a 3:1 molar ratio of acetic anhydride: aldehyde.

Under the optimized reaction conditions, a wide range of aromatic aldehydes bearing electron-donating and electron-withdrawing groups were reacted with acetic anhydride in the presence of MPA-DAZY under solvent-free conditions at 45–55 °C and the corresponding 1,1-diacetates were obtained in good to excellent yields (80–98%) in 60–110 min (Table 3). The results showed that the nature of substituent (electron-withdrawing or electron-donating) has no significant effect on the catalyst activity. In the case of 2-hydroxybenzaldehyde (Table 3, entry 3), only the aldehyde group was reacted with acetic anhydride and no acetate was detected in the reaction mixture.

The ability of NaY zeolite (250 mg), DAZY (250 mg) and molybdophosphoric acid (1 mol%) as catalyst was also investigated in the protection of 3-nitrobenzaldehyde with Ac_2O . The results showed that the amount of the corresponding 1,1-diacetate was 30%, 42% and 65%, respectively. These observations clearly showed that upon encapsulation of molybdophosphoric acid in the zeolite cavity, its catalytic activity increases.

Moreover, the ability of this catalyst was investigated in the deprotection of 1,1-diacetates in refluxing acetonitrile (Table 3). The results showed that this catalytic system is efficient for deprotection of 1,1-diacetates to their corresponding aldehydes in good yields in the presence of 2 mol% of the catalyst. The lower yield for 1,1-diacetates bearing substituent in the *ortho* position of the aromatic ring can be attributed to the difficulty in the entering in the zeolite cavity.

3.2. Catalyst reusability

The reusability of MPA-DAZY catalyst was investigated in the multiple sequential reaction of 3-nitrobenzaldehyde with acetic anhydride. At the end of the each reaction, the catalyst was separated by simple filtration, washed with ethyl acetate and Et_2O and dried carefully before using it in the next run. After using of catalyst for four consecutive times, the yields were 75% (Table 4). The filtrates were collected for determination of Mo leaching (measured by

AAS). The results showed that Mo catalyst is leached from zeolite and therefore, the yield decreased (Table 4).

4. Conclusion

In summary, in this paper we reported a mild and efficient protocol for the protection of aldehydes with acetic anhydride under solvent-free conditions and 1,1-diacetates were obtained in good to excellent yield. This catalytic system was also used for deprotection of 1,1-diacetates refluxing acetonitrile. The advantages of this catalytic system are high catalytic activity, environmentally benign nature of the reaction and reusability of the catalyst.

References

- [1] W.T. Greene, P.G.M. Wuts, *Protective Groups in Organic Synthesis*, third ed., Wiley, New York, 1999.
- [2] K.S. Kochhar, B.S. Bal, R.P. Deshpande, S.N. Rajadhyaksha, H.W. Pinnick, *J. Org. Chem.* 48 (1983) 1765.
- [3] Frick J.G., Jr., J.R., Harper, *J. Appl. Polym. Sci.* (1984) 1433.
- [4] M.J. Gregory, *J. Chem. Soc.* (1970) 1201.
- [5] F. Freeman, E.M. Karcherski, *J. Chem. Eng. Data* 22 (1977) 355.
- [6] T.S. Jin, G. Sun, Y.W. Li, T.S. Li, *Green Chem.* 4 (2002) 255.
- [7] H.M.S. Kumar, B.V.S. Reddy, P.T. Reddy, J.S. Yadav, *J. Chem. Res. (S)* (2000) 86.
- [8] S. Gowravaram, S. Abraham, T. Ramalingam, J.S. Yadav, *J. Chem. Res. (S)* (2002) 144.
- [9] T.S.G. Jin, Y. Du, T.S. Li, *Ind. J. Chem., Sect. B* 37 (1998) 939.
- [10] J.K. Michie, J.A. Miller, *Synthesis* (1981) 824.
- [11] C. Wang, M. Li, *Synth. Commun.* 32 (2002) 3469.
- [12] B. Karimi, H. Seradj, R.G. Ebrahimi, *Synlett* (2000) 623.
- [13] G.A. Olah, C.S. Mehrotra, *Synthesis* (1982) 962.
- [14] S.V. Rajn, *J. Chem. Res. (S)* (1996) 68.
- [15] M.V. Joshi, C.S. Narasimban, *J. Catal.* 141 (1993) 308.
- [16] T.S. Jin, Y.R. Ma, Z.H. Zhang, T.S. Li, *Synth. Commun.* 27 (1997) 3379.
- [17] H. Firouzabadi, N. Iranpoor, F. Nowrouzi, K. Amani, *Tetrahedron Lett* 44 (2003) 3951.
- [18] G.P. Romanelli, H.J. Thomas, G.T. Baronetti, J.C. Autino, *Tetrahedron Lett* 44 (2003) 1301.
- [19] M. Curini, F. Epifano, M.C. Marcotullio, O. Rosati, M. Nocchetti, *Tetrahedron Lett* 43 (2002) 2709.
- [20] K.L. Chandra, P. Saravanan, V.K. Singh, *Synlett* (2000) 359.
- [21] V.K. Aggarwal, S. Fonquerna, G.P. Vennall, *Synlett* (1998) 849.
- [22] M.D. Carrigan, K.J. Eash, M.C. Oswald, R.S. Mohan, *Tetrahedron Lett* 42 (2001) 8133.
- [23] B.C. Ranu, J. Dutta, A. Das, *Chem. Lett* 32 (2003) 366.
- [24] D.H. Aggen, J.N. Arnold, P.D. Hayes, N.J. Smoter, R.S. Mohan, *Tetrahedron* 60 (2004) 3675.
- [25] G. Smitha, C. Sanjeeva Reddy, *Tetrahedron* 59 (2003) 9571.
- [26] A.R. Hajipour, A. Zarei, A.E. Ruoho, *Tetrahedron Lett* 48 (2007) 2881.
- [27] M.M. Heravi, K. Bakhtiari, F.F. Bamoharram, *Catal. Commun.* 7 (2006) 499.
- [28] J.R. Satam, R.V. Jayaram, *Catal. Commun.* 8 (2007) 1414.
- [29] A.T. Khan, S. Islam, A. Majee, T. Chattopadhyay, S. Ghosh, *J. Mol. Catal. A: Chem.* 239 (2005) 158.
- [30] A. Ziyaei, N. Azizi, M.R. Saidi, *J. Mol. Catal. A: Chem.* 238 (2005) 138.
- [31] J.S. Yadav, B.V.S. Reddy, P. Sreedhar, G. Kondaji, K. Nagaiah, *Catal. Commun.* 9 (2008) 590.
- [32] A.R. Hajipour, L. Khazdooz, A.E. Ruoho, *Catal. Commun.* 9 (2008) 89.
- [33] R. Ballini, M. Bordoni, G. Bosica, R. Maggi, G. Sartori, *Tetrahedron Lett* 39 (1998) 7587.
- [34] B. Sulikowski, R. Rachwalik, *Appl. Catal. A: Gen.* 256 (2003) 173–182.
- [35] H. Van Bekkum, E.M. Flanigen, P.A. Jacobs, J.C. Jansen, *Introduction to zeolite science and practice*, 2001, p. 103.
- [36] S.R. Mukai, T. Masuno, I. Ogina, K. Hashimoto, *Appl. Catal. A: Gen.* 165 (1997) 219.
- [37] M. Moghadam, S. Tangestaninejad, V. Mirkhani, I. Mohammadpoor-Baltork, M. Moosavifar, *Appl. Catal. A: Gen.* 358 (2009) 157.
- [38] N.M. Nagy, M.A. Jacob, J. Konya, S. Antus, *Appl. Clay. Sci.* 22 (2002) 213.
- [39] Z.H. Zhang, T.S. Li, C.G. Fu, *J. Chem. Res. (S)* (1997) 174.
- [40] G.E. Negron, L.N. Palacios, D. Angeles, L. Lomas, R. Gavino, *J. Braz. Chem. Soc.* 16 (3A) (2005) 490.
- [41] T.S. Jin, Y.R. Ma, X. Sun, D. Liang, T.S. Li, *J. Chem. Res. (S)* (2000) 96.