



ELSEVIER

Contents lists available at SciVerse ScienceDirect

Comptes Rendus Chimie

www.sciencedirect.com



Preliminary communication/Communication

Polyvinylpyrrolidone-bound boron trifluoride: A highly efficient catalyst for acylation of alcohols, phenols and trimethylsilyl ethers by acetic anhydride

Masoud Mokhtary^{a,*}, Mohammad Qandalee^b, Faranak Najafizadeh^c^a Department of Chemistry, Rasht Branch, Islamic Azad University, Rasht, Iran^b Department of Biology, Garmsar Branch, Islamic Azad University, Garmsar, Iran^c Department of Chemistry, Science and Research, Amol Branch, Islamic Azad University, Amol, Iran

ARTICLE INFO

Article history:

Received 2 October 2011

Accepted after revision 25 January 2012

Available online 28 February 2012

Keywords:

Acylation

Polyvinylpyrrolidone

Boron trifluoride

Alcohols

Acetic anhydride

ABSTRACT

A highly efficient method for the acylation of alcohols, phenols and trimethylsilyl ethers with acetic anhydride is described using polyvinylpyrrolidone-bound boron trifluoride (PVPP-BF₃) under mild and heterogeneous conditions at room temperature in good to excellent yields. The polyvinylpyrrolidone-boron trifluoride complex shows more water tolerant, non-corrosive and stable solid catalyst elevated Lewis acid properties.

© 2012 Académie des sciences. Published by Elsevier Masson SAS. All rights reserved.


1. Introduction

Ester synthesis reactions are usually conducted with the aid of acid or base catalysts, so the employment of catalyst or promoters that are suitably active but also compatible with other functional groups is of great importance [1]. The protection of alcoholic and phenolic hydroxyl group is an important transformation in organic synthesis [2]. Typically, acylation of alcohols is performed with acetyl chloride or acetic anhydride in the presence of catalysts such as Et₃N and pyridine [3]. A variety of catalysts such as silica gel supported sulfuric acid [4], *p*-toluene sulphonic acid [5], ZnCl₂ [6], CoCl₂ [7], Sc(OTf)₃ [8], TaCl₅ [9], montmorillonit K10 [10], HY zeolite [11], In(OTf)₃ [12], Cu(OTf)₂ [13], Yittria-Zirconia based Lewis acid [14], InCl₃/Mont.K10 [15], Manganese(III) bis(2-hydroxyanil)acetylacetonato complex

[16], Silica Sulfate [17], *p*-MeC₆H₄SO₂NBr₂ [18], DBDMH or TCCA [19], H₆P₂W₁₈O₆₂·24 H₂O [20], ionic liquid based on morpholin [21] borated zirconia [22] and DMAP.saccharin [23] are also known to catalyze the acylation of alcohols. However, most of these methods suffer from at least one of the following disadvantages: vigorous reaction conditions, high cost and toxicity of the reagent, tedious work-up procedures, unsatisfactory yields, and instability and hygroscopic nature of the reagent. The most synthetically versatile methodology for (trans) esterification is provided by Lewis acids, due to their mildness, simplicity in operation and catalytic capabilities. Polymer supported catalysts and reagents have become popular in organic synthesis over the past decades. The high catalytic activity, low toxicity, stability, their recyclability, and environmentally safe conditions make the use of a polymer supported reagent attractive alternatives to conventional reagents. Also, the application of polymer supported reagents and catalysts has received special attention, due to easy work up of reaction products and some selectivity which is undoubtedly attractive features of this methodology [24]. In the course

* Corresponding author.

E-mail addresses: mmokhtary@iaurasht.ac.ir, masoud.mokhtary@gmail.com (M. Mokhtary).



Scheme 1. Acylation of alcohols, phenols and trimethylsilyl ethers in acetonitrile via PVPP-BF₃.

of our research on amidation of benzhydrol with nitriles via polyvinylpolypyrrolidone-bound boron trifluoride (PVPP-BF₃) [25], in this work we found that PVPP-BF₃ can be used as a recyclable and more efficient catalyst for acetylation of alcohols, phenols and trimethylsilyl ethers in excellent yields at room temperature (Scheme 1).

2. Experimental

All chemicals were purchased from Merck chemical company. Melting points were recorded on an electro thermal melting point apparatus. The NMR spectra were recorded in CDCl₃ with TMS as an internal standard on a Bruker advance DRX 400 MHz spectrometer. IR spectra were determined on a SP-1100, P-UV-Com instrument. Purity determination of the products was accomplished by TLC on silica gel poly gram SIL G/UV 254 plates. Products were identified by comparison IR and NMR spectra, with those reported for authentic samples.

2.1. Catalyst preparation

In this method, boron trifluoride etherate was immobilized on polyvinylpolypyrrolidone to give a stable polymeric Lewis acid reagent according to our previous article [25]. To a suspension of PVPP (3 g) in CH₂Cl₂ (25 ml), a solution of BF₃·OEt₂ (5 ml) in CH₂Cl₂ (15 ml) was added dropwise and the mixture stirred for 1 h at room temperature. The resulting resin was filtered and washed with CH₂Cl₂ (2 × 10 ml) and dried in a vacuum desiccator to give a stable and non-hygroscopic powder.

2.2. General procedure for acetylation of alcohols and phenols

To a stirred mixture of the alcohol (1 mmol), Ac₂O (2 mmol) and CH₃CN (3 ml) was added PVPP-BF₃ (0.025 g) and stirring continued at room temperature. The progress of the reaction was monitored by TLC. After completion of the reaction, dichloromethane (15 ml) was added and the reaction mixture was filtered. The organic phase was washed with saturated NaHCO₃ solution (15 ml), dried over anhydrous Na₂SO₄ and evaporated to give the pure acylated product. The isolated products were characterized by spectral studies (FT-IR and NMR). The spectra were compared with those of standard esters. The yield was calculated as mmol of purified product with respect to mmol of initial alcohol. The reaction times and yields of the products are presented in Table 3.

2.3. General procedure for acetylation of silylated alcohols and phenols

To a stirred mixture of the silylated alcohol or silylated phenol (1 mmol), Ac₂O (2 mmol) and CH₃CN (3 ml) was

added PVPP-BF₃ (0.05 g) and stirring continued at room temperature. The progress of the reaction was monitored by TLC. After completion of the reaction, dichloromethane (15 ml) was added and the reaction mixture was filtered. The organic phase was washed with saturated NaHCO₃ solution (15 ml), dried over anhydrous Na₂SO₄ and evaporated to give the pure acylated product. The isolated products were characterized by spectral studies (FT-IR and NMR). The spectra were compared with those of standard esters. The reaction times and yields of the products are presented in Table 3.

2.4. Selected characterization data

2.4.1. 2-phenylethyl acetate (Table 3, entry 1)

Yield 99%; IR (KBr) ν : 2958, 2925, 1745, 1529, 1457, 1375, 1037, 746 cm⁻¹. ¹H NMR (CDCl₃) δ = 2.06 (s, 3H), 2.95 (t, 2H, *J* = 7.2), 4.29 (t, 2H, *J* = 7.2), 7.24–7.35 (m, 5H) ppm. ¹³C NMR (CDCl₃) δ = 170.96, 137.80, 128.85, 128.47, 126.53, 64.89, 34.07, 20.93.

2.4.2. 4-isopropylbenzyl acetate (Table 3, entry 4)

Yield 97%; IR (KBr) ν : 2958, 2861, 1743, 1457, 1230, 1027, 819, 736 cm⁻¹. ¹H NMR (CDCl₃) δ = 1.27 (d, 6H), 2.12 (s, 3H), 2.9 (m, 1H), 4.68 (s, 2H), 7.24 (d, 2H, *J* = 8.4), 7.31 (d, 2H, *J* = 8.4) ppm. ¹³C NMR (CDCl₃) δ = 171.02, 151.24, 136.10, 127.32, 126.59, 72.47, 34.55, 24.85, 20.11.

2.4.3. *p*-nitrobenzene acetate (Table 3, entry 14)

Yield 99%; IR (KBr) ν : 2927, 2852, 1762, 1523, 1344, 1197, 1099, 858 cm⁻¹. ¹H NMR (CDCl₃) δ = 2.37 (s, 3H), 7.28 (d, 2H, *J* = 7.2), 8.27 (d, 2H, *J* = 7.2) ppm. ¹³C NMR (CDCl₃) δ = 168.46, 155.36, 146.15, 125.24, 122.48, 21.16.

2.4.4. *m*-tolyl acetate (Table 3, entry 15)

Yield 99%; IR (KBr) ν : 2927, 2861, 1770, 1589, 1457, 1371, 1145, 1014, 943, 784 cm⁻¹. ¹H NMR (CDCl₃) δ = 2.31 (s, 3H), 2.38 (s, 3H), 6.9–7.3 (m, 3H) ppm. ¹³C NMR (CDCl₃) δ = 169.85, 149.42, 135.53, 129.99, 125.18, 121.28, 118.63, 21.16, 20.91.

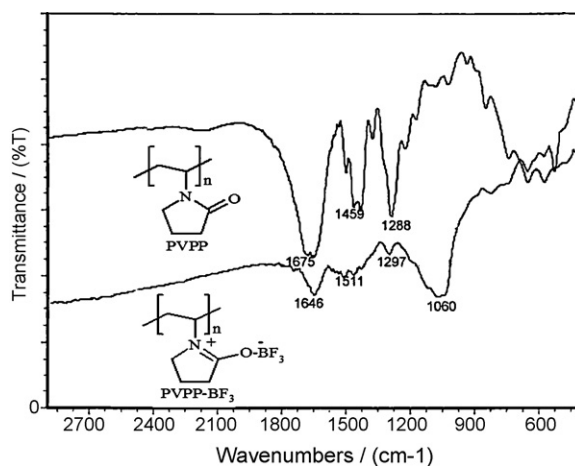


Fig. 1. The FT-IR spectrum of polyvinylpolypyrrolidone (PVPP) and (PVPP-BF₃) complex.

Table 1
Effect of solvents on acylation of 2-phenylethanol (1 mmol) using acetic anhydride (2 mmol) promoted by PVPP-BF₃.^a

Entry	Solvent	Time (h)	Conversion ^b (%)
1	CH ₂ Cl ₂	4	48
2	Et ₂ O	2.5	76
3	CH ₃ CN	0.5	99
4	CH ₃ NO ₂	2.5	68
5	<i>n</i> -hexane	3	56

^a All reactions were carried out using 0.025 g of the polymeric reagent.

^b The conversion was determined by GC analysis of the crude product.

Table 2
Effect of PVPP-BF₃ on acylation of 2-phenylethanol (1 mmol).^a

Entry	Ac ₂ O (mmol)	PVPP-BF ₃ (g)	Conversion ^b (%)
1	1	0.015	42
2	2	0.015	68
3	3	0.015	71
4	1	0.025	76
5	2	0.025	99

^a Reactions were carried out in acetonitrile at room temperature in 0.5 h.

^b The conversion was determined by GC analysis of the crude product.

3. Results and discussion

Characterization of the Lewis acid sites present on the polymer was performed by recording the FT-IR spectrum of PVPP-BF₃, which shows a strong broad absorption at 1000–1060 cm⁻¹ for the BF bonds and a moderate absorption at 1646 cm⁻¹ corresponds to the imine group on the backbone (Fig. 1). The capacity of the reagent was determined by titration and found to be 10 mmol/g,

whereas its silica supported analogue has a loading capacity of less than 4 mmol/g [26,27]. Despite that BF₃·Et₂O, PVPP-BF₃ is more water tolerant, non-corrosive and stable solid catalyst elevated Lewis acid property. Interestingly, this reagent gives not only excellent yields of the products but also PVPP-BF₃ is easily regenerated and can be reused several times and retains its activity after several months of storage. To select the best solvent, the acylation of 2-phenylethanol was studied in a variety of organic solvents such as dichloromethane, acetonitrile, nitromethane, diethylether, and *n*-hexane. Among them, the reaction in acetonitrile proceeds faster than other organic solvents in the same concentration of solvent (Table 1). As seen in Table 2, the optimized stoichiometric ratio of ROH: Ac₂O was found to be 1:2 using 0.025 g of the PVPP-BF₃ in acetonitrile at room temperature. All reactions were carried out under the optimized conditions, and the results are summarized in Table 3. Excellent yields were obtained for a variety of primary, secondary, tertiary, benzylic alcohols, and substituted phenols. Primary alcohols were acetylated faster than secondary and tertiary alcohols (entries 1, 11, and 12, Table 3). The influence of the presence of substituents investigated and the results showed that the reactions were relatively affected by electronic and steric factors. Table 3, shows that benzylic alcohols and phenols with electron-donating groups were converted to the corresponding acetates in shorter time than those with electron-withdrawing groups. Also, a series of silylated alcohols and phenols are treated with acetic anhydride under catalysis by the PVPP-BF₃ (entries 21–25, Table 3). To conclude, PVPP-BF₃ is a good one-pot desilylation-acetylation catalyst for a wide range of silylated alcohols and phenols. It is reasonable to assume


Table 3
Acylation of different alcohols, phenols and trimethylsilyl ethers using of PVPP-BF₃.

Entry	Substrate	Product ^a	Time (h)	Yield (%) ^b
1	C ₆ H ₅ CH ₂ CH ₂ OH	C ₆ H ₅ CH ₂ CH ₂ OAc	0.5	99
2	C ₆ H ₅ CH ₂ OH	C ₆ H ₅ CH ₂ OAc	1	99
3	4-MeOC ₆ H ₄ CH ₂ OH	4-MeOC ₆ H ₄ CH ₂ OAc	1	98
4	4-Pr ^t -C ₆ H ₄ CH ₂ OH	4-Pr ^t -C ₆ H ₄ CH ₂ OAc	1.5	97
5	2-Cl-C ₆ H ₄ CH ₂ OH	2-Cl-C ₆ H ₄ CH ₂ OAc	1	97
6	4-Cl-C ₆ H ₄ CH ₂ OH	4-Cl-C ₆ H ₄ CH ₂ OAc	2	99
7	4-F-C ₆ H ₄ CH ₂ OH	4-F-C ₆ H ₄ CH ₂ OAc	2	99
8	4-NO ₂ -C ₆ H ₄ CH ₂ OH	4-NO ₂ -C ₆ H ₄ CH ₂ OAc	2	99
9	4-Bu ^t -C ₆ H ₄ CH ₂ OH	4-Bu ^t -C ₆ H ₄ CH ₂ OAc	1.5	98
10	2,4-Cl ₂ -C ₆ H ₃ CH ₂ OH	2,4-Cl ₂ -C ₆ H ₃ CH ₂ OAc	1.5	99
11	(CH ₃ CH ₂ CH ₂ CH ₂) ₂ CHOH	(CH ₃ CH ₂ CH ₂ CH ₂) ₂ CHOAc	2	96
12	C ₆ H ₅ CH ₂ C(CH ₃) ₂ OH	C ₆ H ₅ CH ₂ C(CH ₃) ₂ OAc	2.5	95
13	C ₆ H ₅ OH	C ₆ H ₅ OAc	2	85
14	4-NO ₂ -C ₆ H ₄ OH	4-NO ₂ -C ₆ H ₄ OAc	2.5	99
15	3-MeC ₆ H ₄ OH	3-MeC ₆ H ₄ OAc	2	99
16	4-MeC ₆ H ₄ OH	4-MeC ₆ H ₄ OAc	1	95
17	4-MeO-C ₆ H ₄ OH	4-MeO-C ₆ H ₄ OAc	0.5	98
18	2-Br-C ₆ H ₄ OH	2-Br-C ₆ H ₄ OAc	2	98
19	4-Cl-C ₆ H ₄ OH	4-Cl-C ₆ H ₄ OAc	1	85
20	2-Et-C ₆ H ₄ OH	2-Et-C ₆ H ₄ OAc	1.5	80
21	C ₆ H ₅ CH ₂ OTMS	C ₆ H ₅ CH ₂ OAc	2.5	96 ^c
22	C ₆ H ₅ CH ₂ CH ₂ OTMS	C ₆ H ₅ CH ₂ CH ₂ OAc	1	97 ^c
23	C ₆ H ₅ OTMS	C ₆ H ₅ OAc	3	85 ^c
24	4-Cl-C ₆ H ₄ OTMS	4-Cl-C ₆ H ₄ OAc	1	84 ^c
25	4-MeO-C ₆ H ₄ CH ₂ OTMS	4-Cl-C ₆ H ₄ CH ₂ OAc	1	96 ^c

^a Reaction conditions: alcohol (1 mmol), acetic anhydride (2 mmol), PVPP-BF₃ (0.025 g), MeCN, r.t.

^b Isolated yields.

^c PVPP-BF₃ (0.05 g) was used.

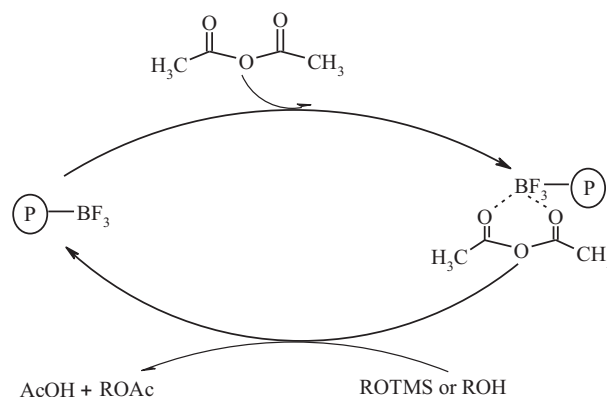

Scheme 2. The proposed mechanism.

Table 4

Comparison of our reagent with some other reagents in acylation of benzyl alcohol.

Entry	Reagent	Conditions	Time (h)	Yield (%)	Ref.
1	Yttria-Zirconia-based-Lewis acid	110–125 °C	4	94	[14]
2	InCl ₃ /mont.K10	50 °C	0.7	92	[15]
3	[Mn(haacac)Cl]	MeNO ₂ , 30 °C	5	97	[16]
4	<i>p</i> -MeC ₆ H ₄ SO ₂ NBr ₂	CH ₂ Cl ₂ , r.t.	1	95	[18]
5	DBDMH or TCCA	CH ₂ Cl ₂ , r.t.	7.5	97	[19]
6	H ₆ P ₂ W ₁₈ O ₆₂ .24 H ₂ O	Toluene, r.t.	0.75	98	[20]
7	Borated zirconia	Toluene /110 °C	4.5	92	[22]
8	PVPP-BF ₃	MeCN, r.t.	1	99	This work

that the present reaction is initiated by Lewis acidity and oxophilicity of PVPP-BF₃ which promotes the acylation reaction via deprotection of trimethyl silyl ether and coordination to oxygen atoms of acetic anhydride and facilitation of C–O cleavage by attacking of hydroxyl group (Scheme 2). In order to learn the catalytic activity of PVPP-BF₃, we compared our obtained results for the acylation of benzyl alcohol with the best of the well-known data from literature as shown in Table 4. The advantages of the described method in comparison with other previously reported catalysts are: the reaction occurs at room temperature with good to high yield of the products, more water tolerant, non-corrosive and stable solid catalyst. To check the reusability of the catalyst, it was employed the acylation of 2-phenyl ethanol fourth cycles under the optimum conditions. The catalyst powder was recovered by filtration, washed with dichloromethane and immediately reused for acylation processes again, taking into account the partial loss of catalyst during the recovery. The second cycle was performed with the recovered catalyst and addition of two equimolecular amount of acetic anhydride gave corresponding ester in 96% yield. The third and fourth cycles were performed with the recovered catalyst similar to above method and 88% and 79% of 2-phenylethyl acetate was obtained respectively. To improve the catalytic activity of catalyst after fourth cycles it is favored to separate the polyvinylpyrrolidone by filtration, washed carefully from dichloromethane and dried, then treated with boron trifluoride etherate again to prepared fresh polyvinylpyrrolidone immobilized

boron trifluoride catalyst. The polymer support can be used several times for the immobilization of boron trifluoride. So, the recyclability of the polymer support together with its biocompatibility makes the method environmentally safe and friendly.

4. Conclusions

We have developed a simple methodology for esterification reaction using PVPP-BF₃ as a high loading of Lewis acid, which is stable, easy to prepared and handle, and represent effective procedure for the acylation of primary, secondary and tertiary alcohols, phenols and trimethylsilyl ethers with acetic anhydride in acetonitrile at room temperature. Excellent yields, easy work-up and reusability and stability of the catalyst are noteworthy advantages of this method.

Acknowledgements

We are thankful to Islamic Azad University, Rasht Branch and Islamic Azad University, Science and Research, Amol Branch for financial assistance in this work.

References

- [1] J. Otera, Esterification, Wiley-VEH Verlag, Weinheim, 2003.
- [2] T.W. Green, P.G.M. Wuts, Protective Groups in Organic Synthesis, 3rd ed, John Wiley and Sons, New York, 1999.
- [3] W. Steglich, G. Hofle, Angew. Chem. Int. Ed. Engl. 8 (1969) 981.

- [4] M.G. Nascimento, S.P. Zanotto, M. Scremin, M.C. Rezende, *Chem. Commun.* 26 (1996) 2715.
- [5] A. Cope, E. Herrick, *Org. Synth.* 4 (1963) 304.
- [6] R. Baker, F. Bordwell, *Org. Synth.* 3 (1955) 141.
- [7] J. Iqbal, R. Srivastva, *J. Org. Chem.* 57 (1992) 2001.
- [8] K. Ishihara, M. Kubota, H. Kurihara, H. Yamamoto, *J. Am. Chem. Soc.* 117 (1995) 4413.
- [9] S. Chandrasekhar, T. Ramachander, M. Takhi, *Tetrahedron Lett.* 39 (1998) 3263.
- [10] T. Li, A. Li, *J. Chem. Soc. Perkin Trans. 1* (1998) 1913.
- [11] R. Ballini, G. Bosica, S. Carloni, L. Ciaralli, R. Maggi, G. Sartori, *Tetrahedron Lett.* 39 (1998) 6049.
- [12] K. Chauhan, C. Frost, I. Love, D. Waite, *Synlett.* (1999) 1743.
- [13] P. Saravanan, V. Singh, *Tetrahedron Lett.* 40 (1999) 2616.
- [14] P. Kumar, R.K. Pandey, M.S. Bodas, S.P. Dagade, M.K. Dongare, A.V. Ramaswamy, *J. Mol. Catal. A Chem.* 181 (2002) 207.
- [15] V. Choudhary, K.Y. Patil, S.K. Jana, *J. Chem. Sci.* 116 (2004) 175.
- [16] M. Salavati-Niasari, S. Hydarzadeh, A. Amiri, S. Salavati, *J. Mol. Catal. A Chem.* 231 (2005) 191.
- [17] T.S. Jin, Y. Zhao, L.B. Liu, Z. Chen, T.S. Li, *Synth. Commun.* 36 (2006) 1221.
- [18] Z. Duan, Y. Gu, Y. Deng, *J. Mol. Catal. A Chem.* 246 (2006) 70.
- [19] M.A. Zolfigol, A. Khazaei, A. Ghorbani Choghamarani, A. Rostami, M. Hajjami, *Catal. Commun.* 7 (2006) 399.
- [20] G.P. Romanelli, D. Bennardi, J. Autino, G. Baronetti, H. Thomas, *Eur. J. Chem.* 5 (2008) 641.
- [21] C. Yue, Q. Liu, T. Yi, Y. Chen, *Monatsh. Chem.* 141 (2010) 975.
- [22] L. Osiglio, G. Romanelli, M. Blanco, *J. Mol. Catal. A Chem.* 316 (2010) 52.
- [23] N. Lu, W.H. Chang, W.H. Tu, C.K. Li, *Chem. Commun.* 47 (2011) 7227.
- [24] S.V. Lev, I.R. Baxendale, R.N. Bream, *J. Chem. Soc. Perkin Trans. 1* (2000) 3815.
- [25] M.M. Lakouraj, M. Mokhtary, *Monatsh. Chem.* 140 (2009) 53.
- [26] K. Wilson, J.H. Clark, *Chem. Commun.* (1998) 2135.
- [27] K. Wilson, D.J. Adams, G. Rothenberg, J.H. Clark, *J. Mol. Catal. A* 156 (2000) 309.