



Account/Revue

Preparation of activated carbon from *Turbinaria turbinata* seaweeds and its use as supercapacitor electrode materials

Marie-Julie Pintor^a, Corine Jean-Marius^a, Valérie Jeanne-Rose^a, Pierre-Louis Taberna^b, Patrice Simon^b, Jean Gamby^c, Roger Gadiou^d, Sarra Gaspard^{a,*}

^a Connaissance et valorisation : chimie des matériaux, environnement, énergie (COVACHIM, M2E), EA 3592, faculté des sciences exactes et naturelles, université des Antilles et de la Guyane, BP 250, 97157 Pointe-à-Pitre cedex, Guadeloupe

^b Centre interuniversitaire de recherche et d'ingénierie des matériaux (CIRIMAT/LCMIE), UMR CNRS 5085, université Paul-Sabatier, bâtiment 2R1, 31062 Toulouse cedex 9, France

^c Laboratoire Interfaces et systèmes électrochimiques, CNRS UPR 15, université Pierre-et-Marie-Curie, Paris-6, Boîte courrier 133, 4, place Jussieu, 75252 Paris cedex 05, France

^d Institut de science des matériaux de Mulhouse (IS2M), CNRS LRC 7228, BP 2488, 15, rue Jean-Starcky, 68057 Mulhouse cedex, France

ARTICLE INFO

Article history:

Received 21 February 2012

Accepted after revision 17 December 2012

Available online 12 February 2013

Keywords:

Supercapacitors
Brown seaweeds
Electrode carbon
Energy storage

ABSTRACT

Turbinaria turbinata brown seaweeds were tested as carbon electrode material in symmetric, electrochemical supercapacitors. The electrochemical properties of the carbon materials were characterised for their application as supercapacitors using cyclic voltammetry, galvanostatic charge/discharge method and electrochemical impedance spectroscopic analyses. Our initial results showed that the optimal behaviour was obtained for the sample prepared by pyrolysis at 800 °C. The average surface area of the carbon was 812 m²/g. Electrochemical tests with an organic electrolyte gave the following interesting results: a capacitance of 74.5 F/g, a specific series resistance of 0.5 Ω cm² and an ionic resistivity of 1.3 Ω cm². These results show the promising capacitive properties of carbon derived from seaweeds and their application in electrochemical supercapacitors.

© 2013 Académie des sciences. Published by Elsevier Masson SAS. All rights reserved.

1. Introduction

In the last decade, the insufficiency of fossil fuels and the coinciding intensification of the greenhouse effect have aroused intensive research into energy storage all over the world.

Among energy storage devices, supercapacitors are the most suited for high-power applications. Supercapacitors are intermediate systems between electrochemical batteries that can accumulate high levels of energy and

convert them to low power through dielectric capacitors, which then can deliver high levels of power [1,2]. Supercapacitors have attracted much attention because they can be charged and discharged quickly, while batteries can only supply bulk energy. Compared to batteries, supercapacitors can store and deliver larger amounts of energy over a longer period of time [3]. These characteristics have spurred an increasing interest in energy storage applications such as: electric vehicles, backup power systems, electronic components and military fields.

Depending on the storage mechanisms, two types of electrochemical capacitors exist: electric double layer capacitors, storing charges by ion accumulation at the electrode/electrolyte interface (Fig. 1) [4] and pseudocapacitors, through electrochemical surface reactions [3].

* Corresponding author.

E-mail addresses: mj pintor@univ-ag.fr (M.-J. Pintor), cjeanmar@univ-ag.fr (C. Jean-Marius), valerie.jeanne-rose@univ-ag.fr (V. Jeanne-Rose), taberna@chimie.ups-tlse.fr (P.-L. Taberna), simon@chimie.ups-tlse.fr (P. Simon), jean.gamby@umpc.fr (J. Gamby), roger.gadiou@uha.fr (R. Gadiou), sgaspard@univ-ag.fr (S. Gaspard).

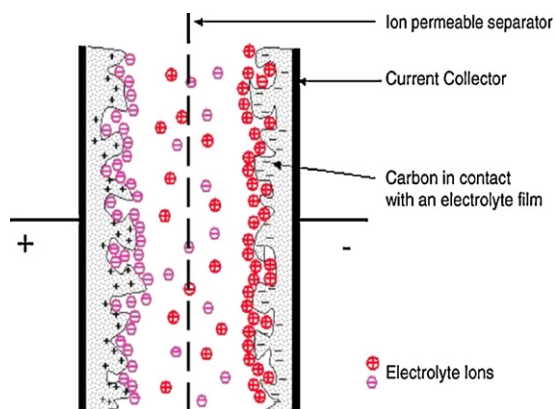


Fig. 1. Representation of an electrochemical double layer capacitor (in its charged state).

Depending on the active materials, three different types of supercapacitors can be encountered:

- carbon/carbon [4];
- metal oxide [5];
- conducting polymers [6].

This work is focused on carbon/carbon supercapacitors.

Carbon as an active material for supercapacitor electrodes has been extensively investigated because of its unique combination of chemical and physical properties, which include its high conductivity, high surface area, good corrosion resistance, and relatively low cost.

Seaweeds constitute a natural source of carbon that is very accessible and cheap. The chemical composition of seaweeds is very versatile, varying with the species and sometimes with the season. In general, they contain carbonate, proteins, lipids, fibre and ash [7]. Because of this adaptability, carbon materials can be prepared from seaweed with different physicochemical characteristics by simple pyrolysis.

Alginate acid, a fibrous substance located in the cellular wall of seaweeds, also offers interesting properties, such as a high oxygen content after pyrolysis. Thus, the oxygen trapped in these carbon electrodes can allow them to adsorb ionic electrolytes more easily [8].

The present work focuses on the feasibility of using carbon prepared from Caribbean seaweeds for electrode materials and studies the relationship between the obtained carbon properties and the performance of the assembled supercapacitor.

2. Experimental

2.1. Preparation of activated carbons

Turbinaria turbinata (Fig. 2) is a tropical brown algae of the *Sargassaceae* family. It generally grows on rocky substrates. The genus has shown promise as a method for removing pollutants from aqueous solutions [9].

T. turbinata biomass was collected in the French West Indies (Saint-François, Guadeloupe) and was sun-dried and crushed. Then, it was filtered to an average particle size



Fig. 2. Pictures of the *Turbinaria turbinata* seaweed.

ranging from 0.4 to 1 mm. The dried seaweed was pyrolysed in a tubular furnace (Thermolyne F 21100) under a nitrogen flow at temperatures between 600 and 900 °C. The heating rate was fixed, and the maximum temperature was held for 3 h. The resulting black solid was then thoroughly washed with 5 M HCl solution for a few hours at 80 °C and washed with water in Soxhlet extractor to ensure that pH stabilisation was reached. We used a similar method to that used in the work of Raymundo-Piñero et al. [10].

The carbons obtained were named CT₆₀₀, CT₇₀₀, CT₈₀₀ and CT₉₀₀.

2.2. Characterisations of activated carbons

2.2.1. Chemical and textural characterisations

The chemical composition of seaweeds is very versatile, fluctuating with the species and the harvest season. Seaweeds are lignocellulosic materials, which are complicated matrices composed of different ratios of cellulose, hemicellulose, lignin and intracellular substances. The chemical composition of the *T. turbinata* seaweeds was determined by performing a standard analysis for lignin (Klason lignin), pentosan (as hemicellulose) and cellulose (Kurschner and Hoffer method), for which the technical processes have already been described by Ouensanga [11].

The Boehm titration method is used to determine the number of acidic and basic surface groups [12]. The determination of the pH_{pzc} of the activated carbons was carried out as previously described [13].

The yield of activated carbon is the percentage (%) amount of activated carbon produced at the end of the activation step. This value indicates the activation process efficiency. Characterisation of activated carbon was performed by nitrogen adsorption/desorption isotherms recorded at 77 K using a Micrometrics ASAP 2020 analyser. Prior to analysis, the samples were degassed in the analyser degassing port for 12 h at 300 °C. The specific surface area, S_{BET} , was calculated using the standard Brunauer–Emmet–Teller (BET) equation [14].

2.2.2. Electrochemical measurements

The electrode was a pellet obtained by mixing 95% of the active material with 5% of the polytetrafluoroethylene

(PTFE) binder, which was dispersed in ethanol [15]. After drying, a symmetric cell was built using a Teflon Swagelok construction, with a fibreglass separator between the electrode pellets. The mass loading and electrodes area were 15 mg/cm^2 and 1.13 cm^2 , respectively.

Tetraethyl ammonium tetrafluoroborate (TEABF_4 , 1 mol/L) in acetonitrile served as the electrolytic solution.

The electrochemical cell was assembled in a glove box under an argon atmosphere to prevent any oxygen and water contamination (O_2 and H_2O contents were less than 1 ppm).

Cyclic voltammetry (CV), galvanostatic charge/discharge and electrochemical impedance spectroscopy (EIS) were performed using a VMP multichannel potentiostat-galvanostat (Biologic, France).

CV tests were performed between 0 and 2.5 V at rates of 5, 10 and 20 mV/s . Galvanostatic charge/discharge curves were measured in the potential range of 0 to 2.5 V at a constant current density of 5 mA cm^{-2} . Impedance measurements were performed in the frequency range from 200 kHz to 10 mHz with a 5 mV voltage amplitude.

3. Results and discussions

3.1. Chemical composition

The results of the chemical analysis of the *T. turbinata* seaweeds are given in Table 1. Hollocellulose, which is cellulose plus hemicellulose, represents the major

Table 1

Botanic composition of *Turbinata turbinata* seaweeds.

Components	Weight (%)
Humidity	13.0
Cellulose	47.3
Hemicellulose	12.2
Lignin	15.8
Extractives	5.1
Ash	6.1

Table 2

Results from chemical surface analyses.

Activated carbons	pH_{pzc}	Total acid groups (mequiv/g)	Total basic groups (mequiv/g)
CT ₆₀₀	2.85	0.836	0.051
CT ₇₀₀	4.08	0.714	0.038
CT ₈₀₀	3.15	0.959	0.050
CT ₉₀₀	3.30	0.853	0.045

component at 59.5%, and the content of extractives are 5.1%. The *T. turbinata* has a lignin content of 15.8%.

During the carbonisation of the lignocellulosic precursors, hemicellulose, cellulose and lignin decompose at different rates within a distinct temperature range [16,17]. These values also allow the prediction that *T. turbinata* seaweeds could be a good candidate for activated carbon synthesis. This composition can play an important role in the properties found for the obtained activated carbons.

Table 2 shows the acidic or basic character of the activated carbons and the pH point of zero charge (pH_{pzc}).

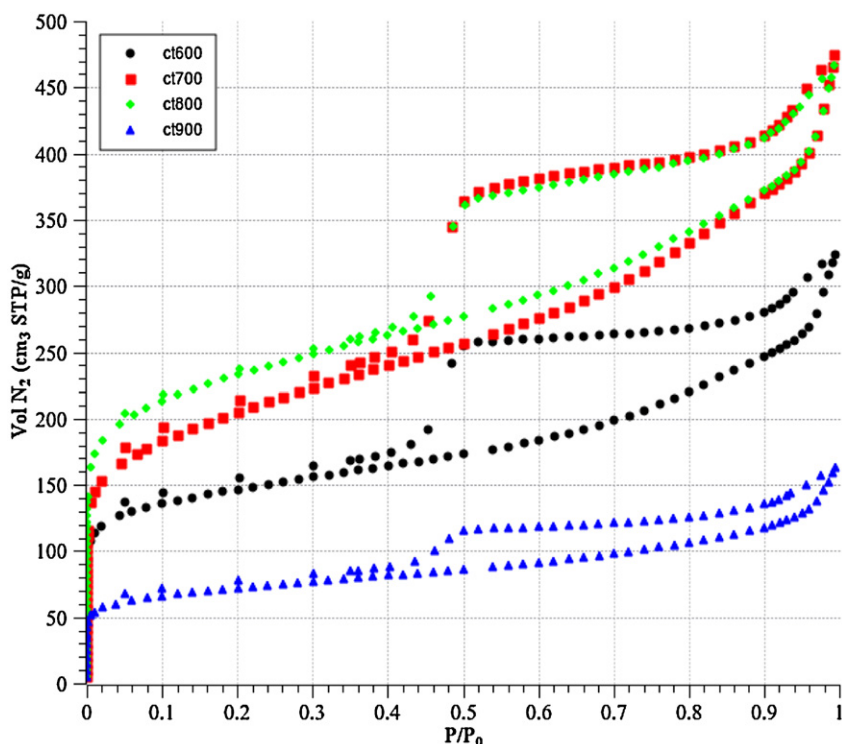


Fig. 3. Adsorption isotherm of nitrogen at 77 K by *T. turbinata* seaweeds pyrolysed at $600 \text{ }^\circ\text{C}$, $700 \text{ }^\circ\text{C}$, $800 \text{ }^\circ\text{C}$, and $900 \text{ }^\circ\text{C}$ for 3 h.

The acidic character of a carbon is associated with oxygen surface complexes or oxygen functionalities such as carboxyls, lactones and phenols. Basic properties of the carbon surface are likely due to:

- functional groups like pyrones, chromenes, ether and carbonyls [13] that contain less oxygen;
- protonated amino groups for nitrogen-rich carbons;
- graphene layers acting as Lewis bases that form electron donor–acceptor complexes with H₂O molecules [18].

The Boehm titration was employed for the determination of active sites on the surface of the following carbon materials: CT₆₀₀, CT₇₀₀, CT₈₀₀ and CT₉₀₀.

The Boehm titration gives both qualitative and quantitative information about acidic groups (in the form of carboxyl, lactone and phenol) and basic groups. From the results obtained in Table 2, it can be observed that the amount of acidic groups was significantly higher than the total amount of basic groups. The results suggest that all carbon materials have an acidic character.

The pH_{pzc} (the point of zero charge) is an important parameter that determines the range of pH sensibility and

allows the surface active sites and adsorption capacities to be predicted [13]. The pH_{pzc} values (Table 2) of the prepared activated carbons are between 2.85 and 4.08.

3.2. Surface and textural characterisations

The porous structure of the prepared carbons was determined by nitrogen adsorption/desorption measurements. Fig. 3 shows the nitrogen adsorption/desorption isotherms of *T. turbinata* seaweeds pyrolysed at 600 °C, 700 °C, 800 °C and 900 °C for 3 hours. Table 3 presents their textural and physical characteristics, including porosity, surface area and pore size.

Compared to the standard BDDT isotherm classification [19], the form of the isotherm may be of type IV for all samples, with an obvious increase in the N₂ amount retained at low values of P/P_0 (< 0.2) and higher relative pressure ($0.1 < P/P_0 < 1$). It is characteristic of a mesoporous structure with a pore size between 2 and 50 nm. In a low-pressure region, the curve is of type II. This can be explained by the formation of a monolayer followed by a multilayer. The intermediate horizontal region in the

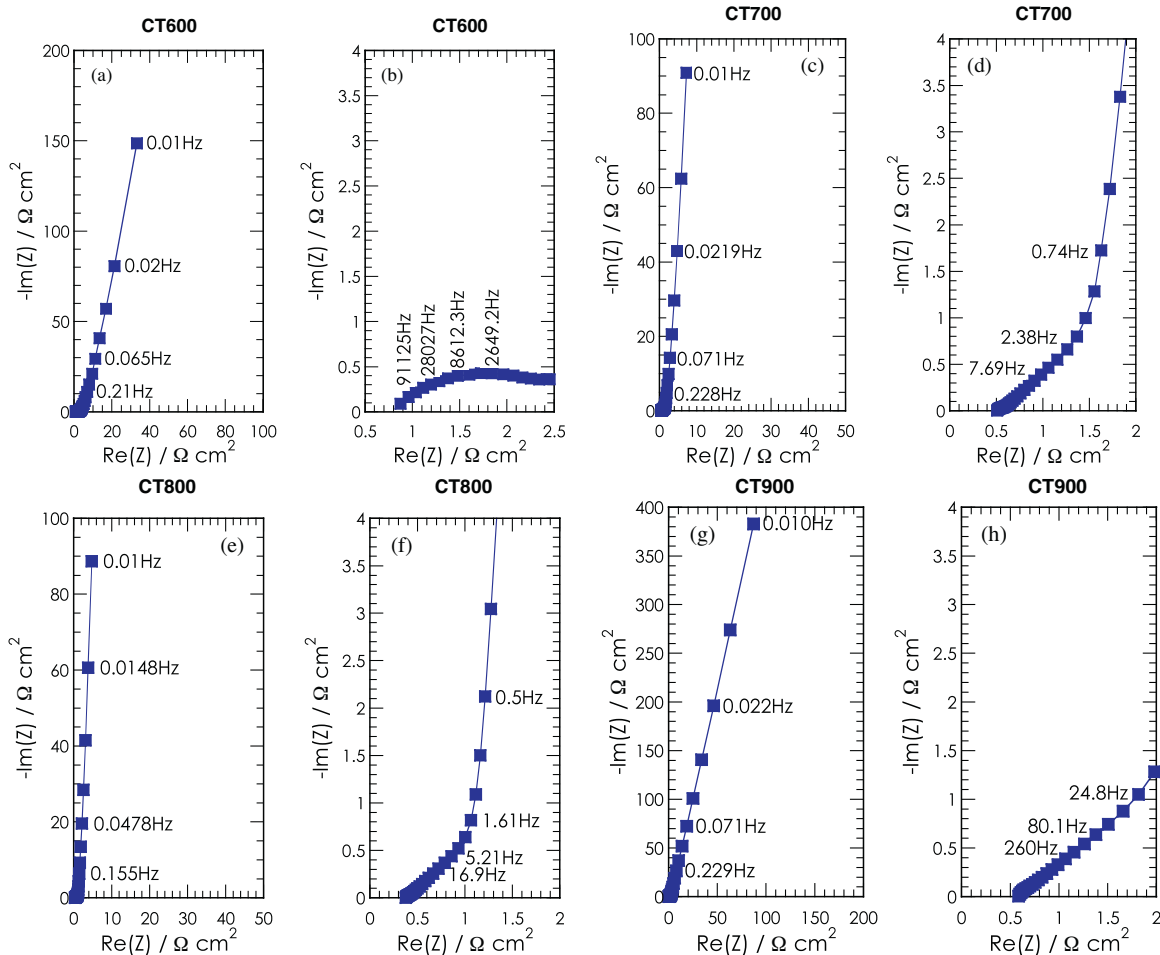


Fig. 4. Impedance spectra between 200 kHz and 10 mHz of symmetric 2-electrode cells containing *T. turbinata* carbon electrodes. At 25 °C, in NET₄BF₄ 1M in acetonitrile. (a), (c), (e) and (g) for respectively CT₆₀₀, CT₇₀₀, CT₈₀₀ and CT₉₀₀. (b), (d), (f) and (h) are respectively a high frequency zoom-in for CT₆₀₀, CT₇₀₀, CT₈₀₀ and CT₉₀₀.

Table 3
Textural characteristics of *T. turbinata* activated carbons.

Samples	Burn-off (%)	Bulk density (g/cm ⁻³)	Mean pore diameter (nm)	BET surface area (m ² /g)	Micropore surface area (m ² /g)	Total volume pore (cm ³ /g)	Micropore volume (cm ³ /g)	Mesopore volume (cm ³ /g)
CT ₆₀₀	53	1.95608	4.1265	530	509	0.62	0.20	0.32
CT ₇₀₀	58	2.13434	4.2406	724	638	0.76	0.26	0.50
CT ₈₀₀	65	2.34718	4.3969	812	698	0.71	0.27	0.44
CT ₉₀₀	70	2.03520	5.3518	258	241	0.24	0.09	0.15

BET: Brunauer–Emmet–Teller.

isotherm corresponds to monolayer formation. The saturation level is reached at a pressure below the saturation vapour pressure. This can be explained by a possible condensation of adsorbent in the tiny capillary pores at pressures below the saturation pressure of the gas [20].

Table 3 shows that as burn-off increases from 53 to 70%, for CT₆₀₀, CT₇₀₀ and CT₈₀₀, the BET surface increases, with the corresponding values of 530, 724 and 812 m²/g. The

micropore volume also increases, with values of 0.20, 0.26 and 0.27 cm³/g for CT₆₀₀, CT₇₀₀ and CT₈₀₀, respectively. For CT₉₀₀, with a burn-off of 70%, a very low BET surface of 258 m²/g and a micropore volume of 0.09 cm³/g are obtained. The even lower BET surface area and micropore volume values compared to the values obtained for CT₇₀₀ and CT₈₀₀ carbons may be due to the achievement of the graphitisation limit and to porous structure collapse.

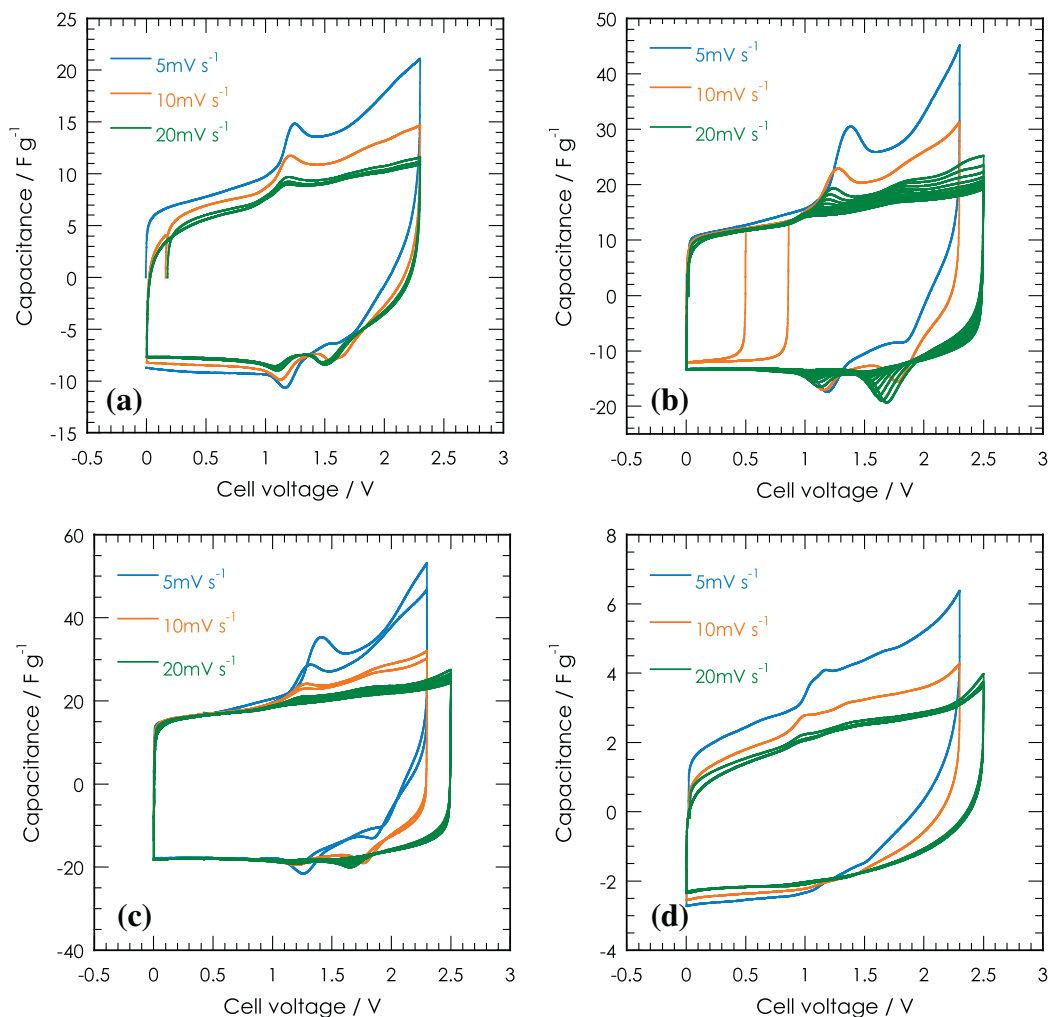


Fig. 5. Cyclic voltammograms of symmetric two-electrode capacitors using CT₆₀₀ (a), CT₇₀₀ (b), CT₈₀₀ (c) and CT₉₀₀ (d) as electrodes in TEABF₄ 1 M in acetonitrile, scan rate 5 mV/s, 10 mV/s and 20 mV/s. Capacitance of cell is normalized respect to the total active material weight.

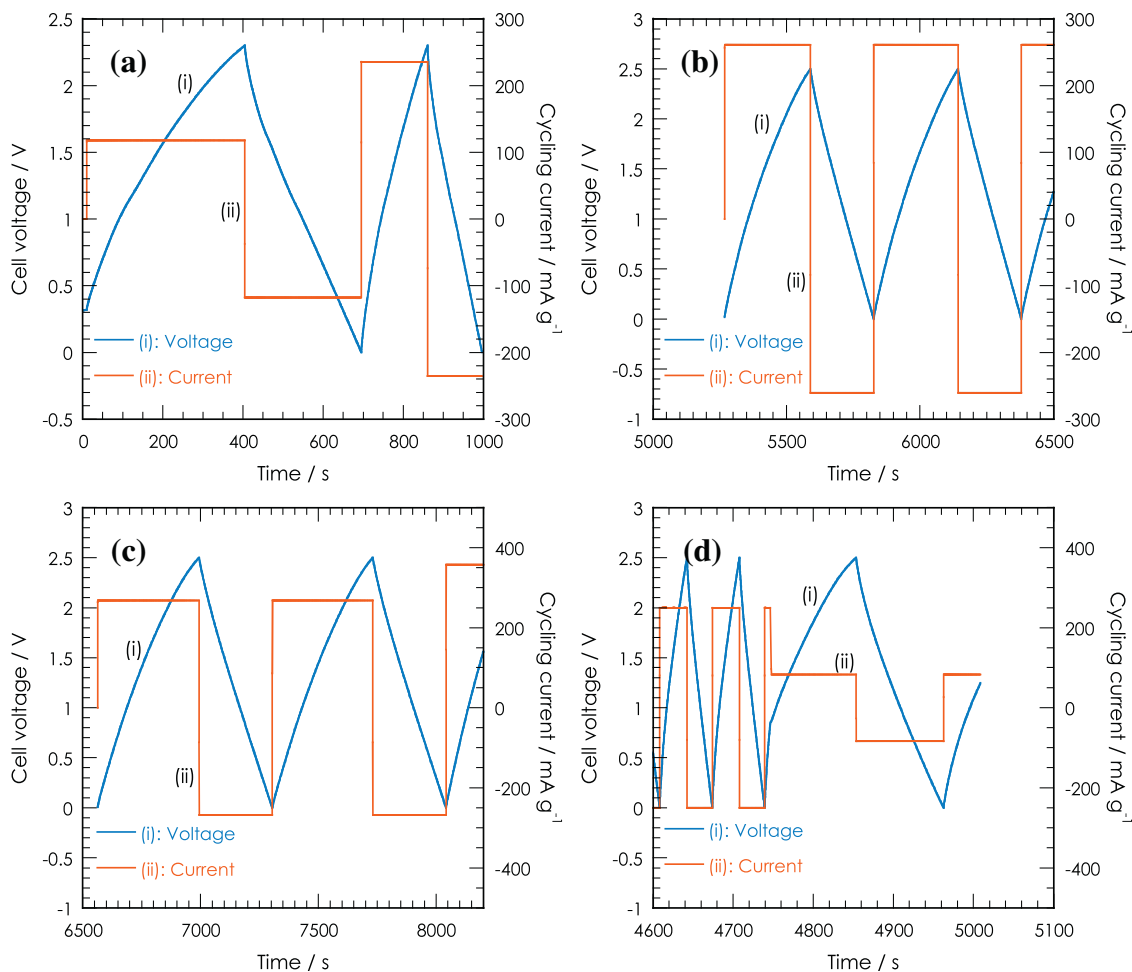


Fig. 6. Charge/discharge galvanostatic cycling at 2.5 V of the seaweed carbon supercapacitor. (a) for CT_{600} , (b) for CT_{700} , (c) for CT_{800} and (d) for CT_{900} .

3.3. Electrochemical characterisations

3.3.1. Analysis of impedance measurements

Impedance measurements were performed in the frequency range from 200 kHz to 10 mHz. Fig. 4 presents the impedance spectra of the cells containing the CT_{600} (a,b), CT_{700} (c,d), CT_{800} (e,f), and CT_{900} (g,h) electrodes. The high frequency resistance values (when the imaginary part is close to zero) are 0.8, 0.65, 0.5 and $0.5 \Omega \text{ cm}^2$ for CT_{600} , CT_{700} , CT_{800} and CT_{900} , respectively. Clearly, the shape of the plots is similar for CT_{700} and CT_{800} ; and it is likewise similar for CT_{600} and CT_{900} . At low frequency, a vertical line close to 90° , indicating a pure capacitive behaviour, should be observed as well as a low ionic resistance in the structure of the electrodes; this ionic migration is observed between the high frequency and the knee frequency [2]. The closer the curve is to the vertical, the more the supercapacitor behaves as an ideal capacitor. Moreover, knee frequencies of 0.46 Hz, 0.73 Hz, 1.0 Hz and 3.5 Hz were measured for CT_{600} , CT_{700} , CT_{800} and CT_{900} , respectively. A slightly different behaviour can be seen for CT_{900} and CT_{600} : the vertical line is not close to 90° , indicating that a leakage resistance due to parasitic irreversible redox

reactions is occurring at the electrode. Fig. 5 also shows the presence of a loop for the CT_{600} sample. The high amplitude of the loop explains the high resistance value. This loop could be ascribed to a pseudo-transfer resistance [21] related to a contact resistance between each activated carbon grain. But this could be also linked to electroactive functional groups at the carbon surface. The difference between the real part of the impedance at the knee frequency and the value of the ESR corresponds to the ionic resistivity of the electrolyte in the pores of the active material. The ionic resistivity is approximately 4.73, 1.13, 0.76, and $2.0 \Omega \text{ cm}^2$ for CT_{600} , CT_{700} , CT_{800} and CT_{900} , respectively. Thus, CT_{800} is the best material in terms of impedance for several reasons: one of the lowest resistances, the lowest activated carbon ionic resistance, no high frequency loop (contact resistance or charge transfer resistance) and without any leakage resistance.

3.3.2. Cyclic voltammetry (CV)

CV measurements were reported between 0 and 2.5 V at different rates: 5, 10 and 20 mV/s. Symmetric supercapacitors were characterised by cyclic voltammetry to observe their profile differences and to determine the

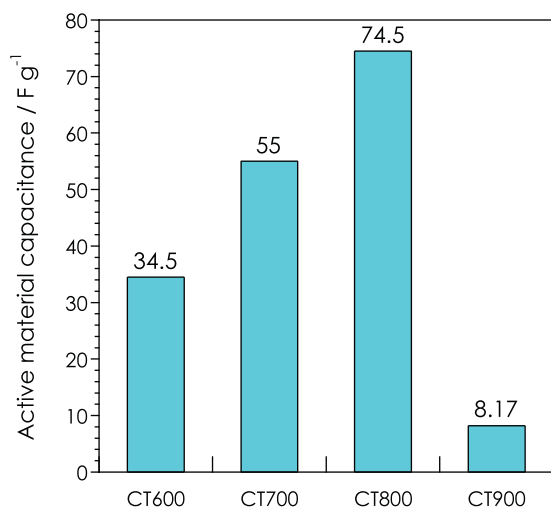


Fig. 7. Evolution of the capacitance of assembled supercapacitors as a function of pyrolysis temperature.

voltage window for charge/discharge cycling. The CV curves (Fig. 5) are quasi rectangular from 0 to 2.5 V. As seen on the CV, small reversible peaks are observed, which can be linked to the functional group at the carbon surface; likewise, it appears that those peaks decrease while the post-thermal treatment was higher. In Table 2, no total acidic group variation was observed, but the pH_{pzc} may explain these results. This is likely because the acidic groups turned it into a less strong acid, and thus less reactive. Nevertheless, the redox potential decreases according to the increase in the number of cycles, leading to a rectangular shape regardless of the thermal treatment.

3.3.3. Galvanostatic cycling

Galvanostatic cycling of supercapacitor cells was performed using a VMP Biologic potentiostat at a constant current density of 5 mA cm^{-2} between 0 and 2.5 V. The electrolyte was used to perform this study in a solution of TEABF_4 (1 M) in acetonitrile. Fig. 6 shows the galvanostatic charge/discharge curves of the prepared samples. The CT_{700} and CT_{800} curves are linear and symmetrical at a constant current density, meaning that no faradaic processes occur in the potential range studied (0–2.5 V). These are other typical characteristics of an ideal capacitor, and the small deviation to linearity is illustrative of a pseudocapacitance contribution.

However, the CT_{600} and CT_{900} curves are neither linear nor symmetrical.

The capacitances were calculated, and specific capacitances of 34.5, 55.0, 74.5 and 8.17 F/g are obtained for CT_{600} , CT_{700} , CT_{800} and CT_{900} , respectively (Fig. 7).

4. Summary

Carbons with a moderate specific surface area and high density were produced by the pyrolysis of seaweeds. The CT_{600} , CT_{700} , CT_{800} and CT_{900} carbons were tested and electrochemically characterised by electrochemical spectroscopy impedance, cyclic voltammetry and galvanostatic cycling. The CV curves are quasi rectangular for all of the samples. The capacitance values are low except for CT_{800} . A low ionic resistivity value was calculated for CT_{700} and CT_{800} ; both seem to have good capacitor behaviour. Textural characteristics making electrolyte ions accessible and enable their adsorption onto the carbon surface could explain this attractive behaviour. The CT_{800} carbon was found to be particularly interesting, with a specific capacitance of 74.5 F/g, an ESR of $0.5 \Omega \text{ cm}^2$ and an ionic resistivity of $0.76 \Omega \text{ cm}^2$ in 1.5 M TEABF_4 in acetonitrile. CT_{800} seems to be an appropriate active carbon material in supercapacitors for energy storage applications. Further investigations are in progress to estimate the cyclability of such activated carbons.

Acknowledgments

Financial support from French Overseas Department Ministry and MESR for PhD funding is acknowledged.

References

- [1] R. Kötz, M. Carlen, *Electrochim. Acta* 45 (2000) 2483.
- [2] B.E. Conway, *Electrochemical Capacitors*, Plenum Press, New York, 1999.
- [3] E. Frackowiak, F. Béguin, *Carbon* 39 (2001) 937.
- [4] J. Gamby, P.L. Taberna, P. Simon, J.F. Fauvarque, M. Chesneau, *J. Power Sources* 101 (2001) 109.
- [5] J.P. Zheng, P.J. Cygan, T.R. Jow, *J. Electrochem. Soc.* 142 (1995) 2699.
- [6] C. Abizzani, M. Mastragostino, F. Soavi, *Electrochim. Acta* 45 (2000) 2273.
- [7] E. Marinho-Soriano, P.C. Fonseca, M.A.A. Carneiro, W.S.C. Moreira, *Bioresour. Technol.* 97 (2006) 2402.
- [8] E. Raymundo-Piñero, F. Leroux, F. Béguin, *Adv. Mat.* 18 (2006) 1877.
- [9] K. Vijayaraghavan, J. Jegan, K. Palanivelu, M. Velan, *Chem. Eng. J.* 106 (2005) 177.
- [10] E. Raymundo-Piñero, M. Cadek, F. Béguin, *Adv. Funct. Mater.* 19 (2009) 1032.
- [11] A. Ouensanga, *Wood Fiber Sci.* 21 (1989) 105.
- [12] H.P. Boehm, E. Diehl, W. Heck, R. Sappock, *Angew. Chem. Int. Ed. Engl.* 76 (1964) 742.
- [13] M.V. Lopez-Ramón, F. Stoeckli, C. Moreño-Castilla, F. Carrasco-Marín, *Carbon* 37 (1999) 1215.
- [14] S. Brunauer, P.H. Emmet, E. Teller, *J. Am. Chem. Soc.* 60 (1938) 309.
- [15] L. Bonnefoi, P. Simon, J.F. Fauvarque, C. Sarrazin, J.F. Sarrau, A. Dugast, *J. Power Sour.* 80 (1999) 149.
- [16] D.M. Mackay, P.V. Roberts, *Carbon* 20 (1982) 87.
- [17] D.M. Mackay, P.V. Roberts, *Carbon* 20 (1982) 136.
- [18] L.R. Radovic, C. Moreno-Castilla, J. Rivera-Utrilla, *Chemistry and physics of carbon*, in: L.R. Radovic (Ed.), *Carbon Material as Adsorbent in Aqueous Solution*, Marcel Dekker, New York, 2001, pp. 1–66.
- [19] S. Brunauer, L.S. Deming, W.S. Deming, E. Teller, *J. Am. Soc.* 62 (1940) 1723.
- [20] K.S. Sing, D.H. Everett, R.A.W. Haul, L. Moscou, R.A. Pierotti, J. Rouquérol, T. Siemieniewska (IUPAC Commission), *Pure Appl. Chem.* 57 (1985) 603.
- [21] X. Andrieu, G. Crépy, L. Josset, in: *Proceedings of the 3rd International Seminar on Double Layer Capacitors and Similar Energy Storage Devices*, Florida Educational Seminar, December, 1993.