

INSTITUT DE FRANCE
Académie des sciences

Comptes Rendus

Physique

Christiane Alba-Simionesco

Organic Glass-Forming Liquids and the Concept of Fragility

Volume 24, Special Issue S1 (2023), p. 177-198


Online since: 3 August 2023

Issue date: 26 April 2024

Part of Special Issue: From everyday glass to disordered solids

Guest editors: Jean-Louis Barrat (Université Grenoble-Alpes, France) and Daniel Neuville (Université de Paris, Institut de physique du globe de Paris, CNRS, France)

<https://doi.org/10.5802/crphys.148>

 This article is licensed under the
CREATIVE COMMONS ATTRIBUTION 4.0 INTERNATIONAL LICENSE.
<http://creativecommons.org/licenses/by/4.0/>



*The Comptes Rendus. Physique are a member of the
Mersenne Center for open scientific publishing*
www.centre-mersenne.org — e-ISSN : 1878-1535



From everyday glass to disordered solids / *Du verre quotidien aux solides désordonnés*

Organic Glass-Forming Liquids and the Concept of Fragility

Les liquides organiques vitrifiables et le concept de fragilité

Christiane Alba-Simionesco ^a

^a Laboratoire Léon Brillouin, Université Paris-Saclay, CEA, CNRS, 91191, Gif-sur-Yvette, France

E-mail: christiane.alba-simionesco@cea.fr (C. Alba-Simionesco)

Abstract. An important category of glass-forming materials is organic; it includes molecular liquids, polymers, solutions, proteins that can be vitrified by cooling the liquid under standard conditions or after special thermal treatments. The range of applications is large from materials to life sciences and recently to electronics. To distinguish them from other systems described in this issue, some specific properties such as the range of their glass transition temperature (T_g), their ability to vitrify and some rules of thumb to locate T_g are presented. The most remarkable property of these liquids is how fast in temperature their viscosity or structural relaxation time increases as approaching T_g . To characterize this behavior and rank the liquids of different strength, C.A. Angell introduced the concept of Fragility nearly 40 years ago. He proposed to classify liquids as fragile or strong in an Arrhenius plot with T_g scaling (the strongest ones have never been observed in organic glasses, except for water under specific conditions). The T_g value and the fragility index of a given liquid can be changed by applying pressure, i.e. changing the density. One can then explore the properties of the supercooled/overcompressed liquid and the glass in a $P-T$ phase diagram. The T_g line corresponds to an isochronic line, i.e. a line at constant relaxation time for different pairs of density-temperature. We observe that all data can be placed on master-curves that depend only on a single density- and species-dependent and T-independent effective interaction energy, $E_\infty(\rho)$. An isochoric fragility index is defined as an intrinsic property of a given liquid, that can help in rationalizing all the correlations between the glass properties below T_g and the viscous slowing down just above T_g from which they are made. Geometrical confinement of liquids is also a way to modify the dynamics of a liquid and the properties of a glass; it corresponds to a large number of situations encountered in nature. Another phase diagram $T-d$ (d defining pore size) can be defined with a non-trivial pore size dependence of the glass transition, which is also strongly affected by surface interactions.

Résumé. Une catégorie importante de matériaux vitrifiables est de nature organique ; elle comprend les liquides moléculaires, les polymères, les solutions, les protéines qui peuvent être vitrifiés par refroidissement du liquide dans des conditions standard ou après des traitements thermiques spéciaux. La gamme d'applications est vaste, allant de la science des matériaux aux sciences de la vie et plus récemment à l'électronique. Afin de les distinguer des autres systèmes décrits dans ce numéro, certaines propriétés spécifiques telles que le domaine de température de transition vitreuse (T_g), leur capacité à former un verre et quelques règles empiriques pour localiser T_g sont présentées. Cependant la propriété la plus remarquable de ces liquides, qui les distinguent des autres classes de matériaux, est la rapidité avec laquelle leur viscosité ou leur temps de

relaxation structural augmente à l'approche de T_g . Afin de caractériser ce comportement et de classer les liquides, C.A. Angell a introduit le concept de fragilité il y a près de 40 ans. Il a proposé de nommer les liquides comme fragiles ou forts dans un diagramme d'Arrhenius en fonction de T_g/T (les plus forts n'ont jamais été observés pour les verres organiques, sauf l'eau sous des conditions particulières). La valeur de T_g et la fragilité d'un liquide donné peuvent être modifiées en appliquant une pression, c'est-à-dire en changeant la densité. On peut alors explorer les propriétés du liquide surfondu et surcomprimé, et celles du verre dans un diagramme de phase $P - T$. La ligne de transition vitreuse correspond à une ligne isochrone, c'est-à-dire une ligne à temps de relaxation constant avec différents couples densité-température. Nous avons observé que toutes les données peuvent être placées sur des courbes maîtresses qui ne dépendent que d'une seule énergie d'activation effective, $E_\infty(\rho)$ dépendante de la densité et de l'espèce et indépendante de la température. Un indice de fragilité isochore est défini comme une propriété intrinsèque d'un liquide donné qui peut aider à rationaliser toutes les corrélations entre les propriétés des verres en dessous de T_g et le ralentissement visqueux juste au-dessus de T_g . Le confinement géométrique des liquides est également un moyen de modifier la dynamique d'un liquide et les propriétés d'un verre ; il correspond à un grand nombre de situations rencontrées dans la nature. Un autre diagramme de phase $T - d$ (d = diamètre des pores) peut être défini avec une dépendance non triviale de la transition vitreuse par rapport à la taille des pores, fortement affectée par les interactions de surface.

Keywords. molecular liquids and glasses, polymers, fragility, density scaling, correlations.

Mots-clés. liquides moléculaires et verres, polymères, fragilité, loi d'échelle en densité, corrélations entre dynamiques rapide et lente.

Manuscript received 26 September 2022, revised 27 January 2023, accepted 21 February 2023.

1. Introduction

The qualification of glass applies to any system from simple liquids to foams, colloids and granular materials, for which structurally arrested states are observed when approaching their glass transition. They all exhibit a growingly slow and heterogeneous dynamics while below the transition the solid made displays out-of-equilibrium behavior with a strong dependence on thermal history. A wide variety of systems can fall into this category described as “a frozen beauty” by C.A. Angell [1, 2]. As pointed out by J. Dyre [3], the phenomenon is so universal that the “glassy” state can be considered as the fourth state of matter requiring a combination of theoretical approaches of solid and liquid states for its understanding; likewise, its experimental study needs the combination of many techniques and observables over a large temporal and spatial range. The most common way to obtain a glass is to cool a liquid at atmospheric pressure. However it is certainly not the only way to form a glass. As shown in [1] many other routes are possible as long as crystallization is prevented: various procedures of vapor deposition on a cold substrate, binary solutions, amorphisation by milling widely used in pharmacology [4], compression and cooling to change the density of the liquid, or confinement at nanoscale.

Among all classes of glasses, organic glasses, (i.e. with Carbon in their chemical formula, and Hydrogen, Oxygen, Nitrogen..) are of special importance, and play a major role in several applications in chemistry or biology. Recently the understanding of their electronic structure and properties became a key parameter for the design of high performance optical and electronic devices, like organic light emitting diodes [5, 6]. However, for all these applications, it remains important to determine the factors driving the formation of a glass and the consequences on its properties. Organic glassforming liquids can be molecular, ionic, liquid crystals, polymer melts or binary-ternary solutions. Many features of the rich phenomenology associated with the glass formation can be also observed in solid materials such as plastic crystals (glassy crystals [7, 8]) or low temperature quadrupolar glasses, out of scope here. The Glass Transition is not a genuine thermodynamic phase transition toward a rigid state. The exact definition of T_g is arbitrary and corresponds to the temperature at which the very slow relaxation dynamics of a supercooled

liquid looks finally stopped at a given experimental time; the system falls out of equilibrium and becomes a glass. Quantitatively, several more or less equivalent definitions of T_g can be found in the literature depending on the experiments: one can define it on cooling as the temperature at which the structural relaxation time τ_α reaches 100s or 1000s, or the viscosity $10^{11} - 10^{13}$ poises; alternatively, on cooling and heating, T_g is the temperature at which a jump in the heat capacity versus T is observed. The latter definition of T_g is usually easily accessible over a narrow temperature range from standard calorimetric scanning measurements (DSC), a very common laboratory technique, for cooling and heating rates between 1 – 20 K/min. When the liquid is cooled at constant pressure, the change of the dynamical properties is so large that it requires an Arrhenius (logarithmic) representation involving an effective activation energy: for organic liquids typically the change of the relaxation time at atmospheric pressure is about 14 orders of magnitude, from the boiling temperature T_b close to the picosecond to T_g as defined above. For the viscosity, the dynamical range is similar but, in the highly viscous regime, it depends on the temperature dependence of the elastic shear modulus G_∞ which differs from one liquid to another [9, 10]. This drastic T-dependence can be decomposed in a first Arrhenius-like behavior at high temperature, slightly above the melting temperature with an almost constant activation energy (with a weak density dependence), E_∞ , $\tau(T) = \tau_\infty \exp(\frac{E_\infty}{T})$, then, below a given temperature T^* [11] and in the supercooled regime, (i.e. below the melting temperature), a super-Arrhenius behavior is observed with a temperature dependent activation energy $E(T)$: $\tau(T) = \tau_\infty \exp(\frac{E(T)}{T})$, with $E(T)$ defined as $E(T) = k_B T * \text{Ln}(\tau(T, P_{atm})/\tau_\infty)$.

Figure 1 left schematically illustrates the viscous slowing down of a molecular liquid with some characteristic temperatures: three are experimentally defined (T_b , T_m , T_g), two are theoretically defined and experimentally avoided (T^* from the Frustration Limited Domain Theory [11], T_c from the Mode Coupling Theory [12]), two are extrapolated and unreachable ones (T_o , the temperature at which η or τ_α might diverge, T_K , the Kauzmann temperature where the liquid configurational entropy vanishes). In Figure 1 right is represented the combination of experimental spectroscopic and scattering techniques required for the study of the viscous slowing down of a molecular liquid (note that for each techniques specific equipments and various methods must be implemented). The different measured dynamical properties might show a different temperature dependence, with a well identified decoupling giving rise to a more complex relaxation map: translation self diffusion evolves less rapidly than the viscosity or molecular reorientation [13–16] above T_g . Likewise with ionic liquids, a decoupling between viscosity and conductivity is evidenced. The degree of departure from an Arrhenius temperature dependence of the structural relaxation is often quantified by the fragility index m proposed by Austeen Angell almost forty years ago. The fragility, or steepness index, is commonly defined at T_g , i.e. at long time scales, by $m = \partial \log_{10}[\tau(T)/\tau_\infty] / \partial (T_g/T)|_{T_g}$.

The usefulness and the robustness of the concept were addressed several times by various authors [17] and nowadays it remains an important criterium to classify systems (see section dedicated below).

The supercooled regime is also characterized by a non-exponential time dependence of the relaxation function, whatever is the technique or the liquid; therefore one cannot consider a single relaxation time but an averaged one, that might span over few decades in time. Many debates took place to understand what this stretching of the relaxation function could reveal about the nature of the dynamics of supercooled liquids. In the 90's [18] several experimental results, using very different observables, allowed to clarify and qualify as heterogeneous the nature of the dynamics. One step further was to consider it as spatially heterogeneous and introduce the notion of a dynamical supramolecular dynamical length scale not directly detected in the pair correlation function defined by the static structure factor.

Finally, a third characteristic of the supercooled liquid is of thermodynamic nature; from specific heat measurements at constant pressure, one can estimate the variation of a configurational entropy S_c . When it is defined as the difference between the entropy of the liquid and the corresponding crystal from the melting temperature down to below T_g it is called an excess entropy often assimilated to the configurational one. As pointed out by Kauzman [19], S_c decreases very rapidly below T_m and might even become negative by extrapolation well below T_g (known as the Kauzman paradox). This excess entropy and its T-dependence are nicely correlated to the viscosity changes in the Adam–Gibbs model [20, 21] allowing to link dynamics and thermodynamics; it predicts a second-order phase transition when $S_c = 0$ at $T = T_{Kauzman}$ with a diverging relaxation time. Many theories of the glass transition [22–26] are relying on this approach even if not fully supporting the original Adam–Gibbs model. Therefore the description of the dynamics with the above equations supposes thermally activated processes with a T-dependence of the activation energy being due to the growth of a length scale of structural or dynamical origine as temperature decreases (see other articles in this issue) and the final cancelling of configurational entropy of liquid suggesting that a thermodynamic phase transition underlies the glass transition.

The search for such a length is subject of many experimental investigations; its experimental determination remains very difficult, indirect and limited to few methods. However a major step has been taken with the observation of its growth when T decreases by Ladieu et al. [27–30] in a large number of molecular liquids. These results are in agreement with the fact that an increasing length would be responsible for the viscous slowing down. Unfortunately its relationship with any structural analogue remains an open question. Moreover, adding to the complexity of the phenomenon, several other lengths have been identified bearing the signature of disorder in the glassy state close to and below T_g and low temperature anomalies [31–34]: in the GHz–THz frequency domain, one can define characteristic lengths from elastic heterogeneities, plastic deformation, the relative strength of shear and bulk moduli, or the ratio of the transverse sound velocity to the boson peak frequency [35–38], any property defining a length scale at which the continuum elastic description breaks down.

It should be noted that this description of viscous slowing down is not the only one [12, 39–42]. Other phenomenological approaches propose to establish a correlation between the relaxation time and another property. For example, the free volume model was widely used for polymers: it supports also by extrapolation below T_g the existence of an underlying phase transition, where the free volume vanishes, but it remains essentially a fitting tool. At variance, other models based on elastic properties, like the shoving model [43], does not lead to a diverging relaxation time below T_g and any underlying phase transition, which makes a strong difference with the models cited above; here the activation energy associated with the flow is correlated to the temperature dependent short-time elastic response, the instantaneous shear modulus G_∞ , which cannot diverge, in a very successful way.

The above description corresponds to the formation of a glass on cooling under standard isobaric conditions, i.e. at atmospheric pressure for experiments versus isochoric conditions for theories. However, one can experimentally explore the properties of the supercooled/overcompressed liquid and the glass in a $P-T$ phase diagram, following isobaric, isothermal or isochoric paths; the phenomenon is then driven by two thermodynamic control parameters, the temperature and the density ρ , which, itself, depends on the temperature. We can then ask the question of their respective contribution to the phenomenon and their coupling. A model-free assessment of the respective contributions of ρ and T in the viscous slowing down have been proposed leading to the collapse of all $\tau_\alpha(\rho, T)$ data on master curves with single density- and species-dependent effective interaction energy $E_\infty(\rho)$ [44] (see Section 3 and Figure 7).

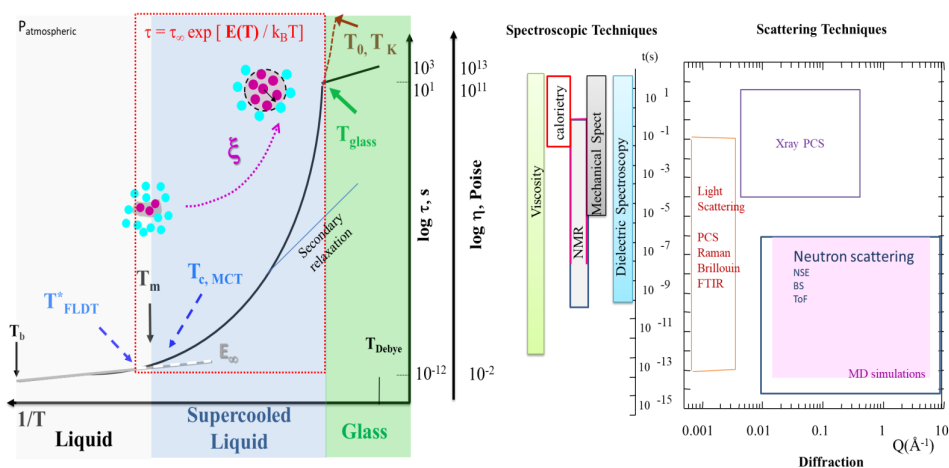


Figure 1. Left: Schematic representation of the viscous slowing down of molecular liquids at atmospheric pressure from the boiling point at T_b to the glass transition temperature T_g . Three dynamical regimes are defined with a different color code, light blue, stable liquid, dark blue supercooled liquid, green for glass. The red square indicates the super-Arrhenius domain, where the activation energy is T -dependent and where a correlation length is increasing down to T_g . The main structural relaxation, so-called α process, and the viscosity are schematically plotted, but other processes, secondary or β relaxations, and decoupling between various dynamical properties can also be observed. Characteristic temperatures describing the viscous slowing down in the literature are added and an increased correlation length is schematically represented; right: spectroscopic and scattering techniques required for the study of the viscous slowing down of a molecular liquid, note that for all of them, specific equipments must be implemented for a given time and space range.

While the description of the viscous slowing down close and at T_g has given rise to numerous experimental and theoretical studies with or without considering an underlying phase transition, the domain at higher temperatures around the onset of the super-Arrhenius regime is much less studied. Other characteristic temperatures are shown in Figure 1 (left). The Frustration Limited Domain Theory (FLDT) and the Mode-Coupling Theory (MCT) are both theories based on the existence of a critical point, respectively T^* and T_c , located well above T_g . T^* is experimentally avoided because of an intrinsic frustration that does not allow the local order of the liquid to be extended; it is defined as a crossover temperature from Arrhenius to super-Arrhenius regime. T_c is defined as a dynamical singularity that can be estimated by adjusting well defined formula and exponent. A more complete overview of the various theories of the glass transition can be found in [26].

To finish this introduction, before going into the description of organic liquids and glasses, it should be noted that there are many empirical formulas to interpolate/extrapolate the dynamic properties with more or less success depending on the temperature range, most of the time using three fitting parameters, see references [45–51] for some of them. For all of them the extrapolation at temperatures above T_m do not match with the liquid properties.

2. Organic Liquids and Glasses

In Organic Liquids and Glasses, the basic unit is a molecule of size, shape and chemical nature tunable at will. They are most often obtained by cooling a liquid well below its melting temperature T_m down to the glass transition temperature T_g at constant pressure with a rate sufficient to avoid the crystallization. Depending on systems, some glasses are obtained easily, with no crystallization on cooling, other might require cooling rate as high as $10^6 - 10^7 K/s$, (as metallic glasses see this issue); water belongs to this latter case. The intermolecular interactions are of short range van der Waals type of the order of 10 kJ/mol i.e. at least more than 10 times less than the energy of intramolecular bonding. In some systems another bonding force prevails, the Hydrogen bond up to few tens of kJ; its energy varies depending on the atoms involved, H-N-O-F, their relative position and distance. For organic materials, one can define the range of temperature where T_g is observed experimentally (at atmospheric pressure): the lowest molecular T_g detected so far by adiabatic calorimetry is for propene (C_3H_6) $T_g = 56K$ [52], and the largest are for sugars, as trehalose (393K) or maltohexaose ($C_{36}H_{62}O_{31}$), $T_g = 448K$. In the latter cases, large uncertainties in the literature come from a possible hydration of the sugar (for trehalose from 348K to 393K), then T_g might decrease by several tens of degrees as water is added [53–57]. Higher T_g 's for sugars can be found (up to 470 – 480 K), but in that case they are made of several units, and not anymore a single molecule.

Polymers are another very important class of so-called organic systems; these macromolecules consist of a covalent chain of a large number of subunits or monomers. Linear or branched, cross-linked or not, rigid or flexible, possessing one or more types of monomers, polymers can have many different characteristics length and time scales (random chain, Kuhn length, monomer). Each of these lengthscales is associated with specific dynamics, such as large-scale relaxations (reflecting collective responses due to connectivity and entanglement) or very local relaxation processes related to the chemical structure of the monomer. The properties of a polymer are determined by an additional control parameter, the molecular weight M_w (also referred to as the number of monomers N) [58–60]. At atmospheric pressure, it is known that the density and the glass transition temperature vary inversely with the molar mass: $T_g = A + \frac{B}{M_w}$, it expresses the fact that the number of end groups sensitive to free volume decreases as M_w increases, leading to an increase in T_g . This increase varies from one polymer to another. Some extreme cases are polystyrene (PS) and polyisobutylene (PIB): in the case of PS, the variation is as large as 130 degrees from the $N=7$ to $N=2000$ monomers accompanied at T_g by a decrease in the density and in the Cp jump; at variance for PIB, the variation of T_g is only of about 13 – 16 degrees for roughly the same change in mass. Due to their larger weight (at least with few monomers) their glass transition temperature is slightly shifted when compared to molecules, the lowest T_g being for the Polydimethylsilane (PDMS, 130 K) to more than 400 K (Polycarbonate 420K, PolyAcidemethacrylic 501K). Although the $1/M_w$ law is robust, it is sometimes necessary to complete it by adding the contribution of the various components of the monomer, like alkyl side chains [61]. Since the glass transition of a polymer is observed at the monomer scale, it keeps a great similarity with that of molecular liquids: T_g depends on thermal history, with a heat capacity jump, a drastic increase of the relaxation time or viscosity in the melt which obeys similar empirical formula (the most known is the Williams–Landel–Ferry that can be converted to the VTF), GHz-THz signatures of the glassy state [62–64]. However, the analogy has some limits due to the role of the chain at larger scale: only in very few cases crystallisation is observed, the heat capacity jump is smaller, the dynamical range is also smaller (10 – 11 decades) in the melt due to possible degradation at high temperature.

For molecular liquids the T_g value changes as well with molecular weight M , as seen in Figure 2 (a) but in a different way; one could find a correlation between M and T_g , $T_g \propto M^{0.6}$

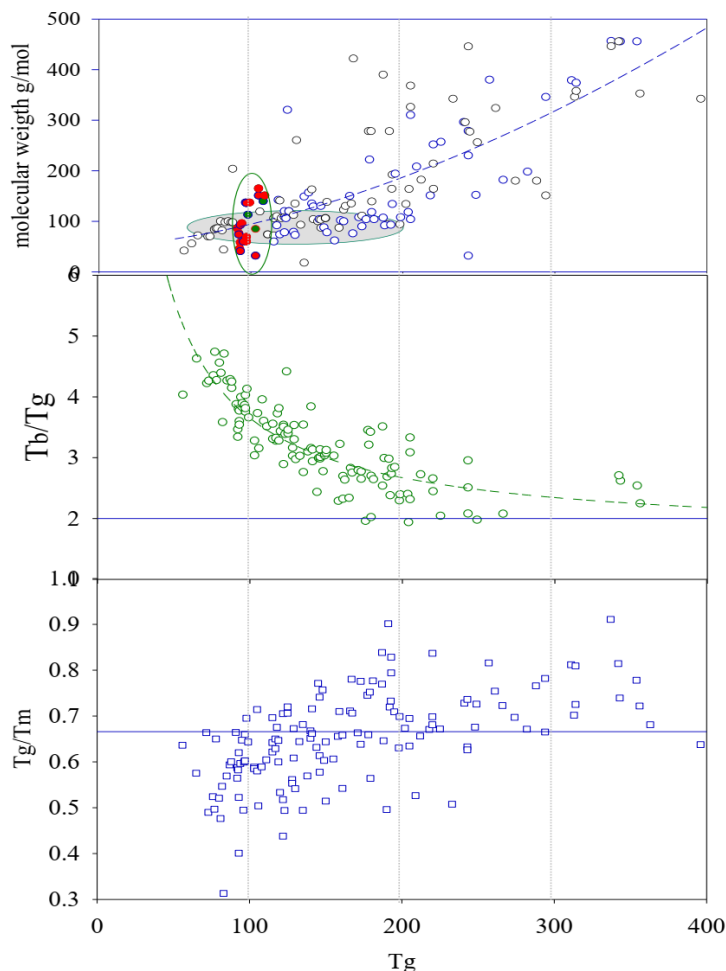


Figure 2. Molecular properties and glass transition location: a) molecular weight of liquids as a function of their T_g , a trend is given by the dashed line indicating a power law dependence $M \propto T_g^{1.67}$ (or $T_g \propto M^{0.6}$). However, many liquids with similar T_g (red zone) or with the same M (grey zone) do not support this relation; b) the ratio $\frac{T_b}{T_g}$ as function of T_g for the same set of liquids when T_b is available, the blue line indicates a ratio equal to 2, the dashed line illustrates how the ratio increases at low T_g values; c) the ratio $\frac{T_g}{T_m}$ as function of T_g for liquids that crystallise, the line indicates the 2/3 rule. Most data are from [65].

(dashed line on the figure) ignoring the specific intermolecular interactions. However, there is a very wide dispersion of points: T_g might vary a lot with liquids of similar M (grey zone in the figure), or liquids with the same T_g might have a huge difference in M , as cumene ($T_g=125\text{K}$, $M=120.2$) and tetrabutyl orthosilicate ($T_g=124\text{K}$, $M=320$). Note that it does not exclude possible relation within a given chemical serie such as alkanes, polyalcohols [65] as soon as the interactions are kept close; note also that water is an exception here with the lowest M ($= 18$) and T_g in the litterature of 136K illustrating the tremendous importance of the H-bond network.

Finally, one should note that proteins have a so-called dynamic transition between 180K and 230K , but not properly speaking a glass transition (no C_p jump detected), distinct from

the denaturation temperature; its signature corresponds to an enhanced mobility and a rapid increase of the mean-square displacement as measured by neutron scattering at 1-4 nsec. For globular proteins, the dynamic transition is related to dynamics and often melting of frozen water trapped inside or at the surface [66–69], which might enhance enzymatic activity.

2.1. Empirical rules for the Glass Formation ability and T_g location

In Figure 2 (b) and (c), one can find several empirical rules of thumb that help to locate the glass transition temperature of a liquid. In a rough approximation, T_g increases as T_b increases [70], changing with the size of the molecule and its interaction strength. However this is just a trend [71, 72] and it does not apply to isomers, when the molecular structure change and the entropic effects become dominant. At least the ratio $\frac{T_b}{T_g}$ is always larger than 2 for all the liquids collected here with a strong increases for low T_g 's; this ratio might be considered as a liquid range index, which surprisingly increases as the glass transition temperature decreases. Another widely used ratio is the $\frac{T_g}{T_m}$ supposed to obey the 2/3 rule. However, in Figure 2 (c), a large dispersion of points is observed and the rule is not valid for liquids having a value of T_g below 150K, with notable extremes cases like cycloheptane (0.31) or sucrose benzoate (0.91). It is implicitly assumed with these plots, that a T_g exists. Moreover very good glass-formers liquids, that do not have a melting point at atmospheric pressure (m-fluoroaniline, dibutylphthalate), or others very bad glass-formers, without a known T_g (methane, Argon, carbone disulfide, benzene..), are not recorded here; it also excludes all cases that are vitrified under specific conditions, for which the rule does not work (water), and illustrates how melting is decoupled from the glass formation. One can apply these rules when the glass transition temperature of a liquid is not known; however it does not predict if it is able to vitrify or not.

A useful rule proposed in the literature to define the ability of a molecular liquid to form a glass under standard cooling rates is the ratio $\frac{T_b}{T_m}$ which should be equal or larger than 2; if we take into account the ratios defined above, one can see that the lower limit of this condition must be rather of the order of 4/3. If one now looks at systems plotted in Figure 2, they all follow this rule, even water obtained from hyperquench or compression procedures, or liquids trapped in emulsions, microemulsions, hard confinement (benzene [73] is an example in Figure 6 (a)). One can ask oneself the interest of this type of rule, with which there is finally only the perfect gases that are excluded or more positively think that all liquids can vitrify as soon as a good trick to avoid crystallisation is found.

What is a good glass former? A system for which crystallization can be avoided during cooling. The mechanisms (nucleation and growth) of crystallization remain central to defining an ability to form a glass or not. The slowest cooling rate needed to bypass crystallization is therefore directly related to the maximum crystallization rate. The easier it is to avoid crystallization, the higher the quality of the glass formed without any risk of nucleation, thus ensuring greater stability of the glass properties in its applications. Crystal growth rates in highly viscous liquids generally show a maximum at $1.2 - 1.3 T_g$, and define the temperature range where it is possible to maintain the system in its supercooled state for very long periods of time. Kinetic and thermodynamic aspects are widely studied in the literature establishing a possible link between viscosity, grain surface morphology and crystal growth [74].

2.2. Structure of Organic Glassforming Liquids

The dramatic change in characteristic times of the dynamics is not accompanied by any measurable signature in the structure or remarkable increase in a static correlation length in the pair correlation function. Indeed, the static structure factor $S(Q)$ changes from one liquid to another because of their distinct molecular shape. This is shown in Figure 3 (a) for a serie of aromatic liquids

over a large wave vector (Q) range at atmospheric pressure and ambient temperature. $S(Q)$ can be splitted into an intramolecular form factor $F(Q)$ acting at high Q describing the intramolecular contribution and an intermolecular contribution $D(Q)$ at low Q 's, i.e. larger distances whose Fourier transform gives the intermolecular pair correlation function $g(r)$ in real space and the local organisation of the first coordination shell. $D(Q)$ is a linear combination of many partial intermolecular atom-atom structure factors and contains all information of the short and medium range order around a molecule. The structure factor $S(Q)$ as function of T down to the glass transition, or as a function pressure at constant temperature up to P_g , exhibits only a smooth evolution with a shift to higher wave vectors due to a density increase and a slight change in shape due to the different temperature dependences of the partial structure factors see Figures 3 (b) and (c) [75]. Figure 4 (a) and (b) illustrate how the main peak of $S(Q)$ and the short range order remains constant at constant density whatever is the temperature and the changes of the relaxation time or the effective activation energy; this is verified for van der Waals molecular liquids and polymers. Discernable supramolecular ordering at the scale of few nanometers, can only be found in systems sensitive to self-organisation such as ionic liquids or hydrogen bonded liquids as soon as this supramolecular organisation is sufficiently larger than intermolecular distance. Figure 4 (c) shows the emergence of a “prepeak” at lower Q 's due to the emergence in the liquid of H-bond induced clusters, and how it is sensitive to temperature. In the latter case, one should notice that despite some analogy between the prepeak observed here and the so-called first sharp diffraction peak observed in silica, representing an intermediate range order, its interpretation and T - ρ dependence are very different.

Finally we should note that even if often the Bragg peaks of the corresponding crystal are located around the position of the main peak in the liquid, the latter does not correspond to a simple broadening of the Bragg peaks because of the disorder, but to very different local structures existing in the liquid in the first/second coordination shell (the crystal nucleus and the local order of a liquid are not equivalent, except in the case of water).

2.3. How to change T_g of a given system?

For a given liquid, several values of T_g can be found, depending on its definition and the experiments carried out (see above): for example, in calorimetry by changing the cooling and/or heating rates, which is equivalent to change the relaxation time of the liquid between 10 and 1000s when equilibrium is reached (it should be kept in mind, however, that the most unambiguous definition of the glass transition temperature is the one made during cooling). In the glassy state, when the timescale of the measurement is short compared to the relaxation time and the system is apparently frozen, the thermodynamic properties continue to evolve. Slightly below T_g , long annealing experiments can be performed to reach equilibrium and a so-called “fictive” temperature is defined, as the temperature at which the value of the thermodynamic properties (such as density, enthalpy or entropy) of the glass would be equivalent to their equilibrium value in the extrapolated liquid.

However in order to vary the value of T_g with the same definition of characteristic time, it is necessary to change the thermodynamic path or impose an additional constraint, while always avoiding crystallization. Thus, for a given system keeping the same intermolecular interactions, we can modify the transition temperature by changing the pressure and thus define a glass transition line in a pressure-temperature diagram as for the lines of fusion or evaporation. The properties of the supercooled and overcompressed liquid can be studied along isobars (with $T_g(P)$) or isotherms defining the glass transition pressure $P_g(T)$ [79–81] or along isochores when the $P - V - T$ equation of state is known. Moreover, similarly to the analysis of dynamical heterogeneities at atmospheric pressure close to T_g , the number of molecules

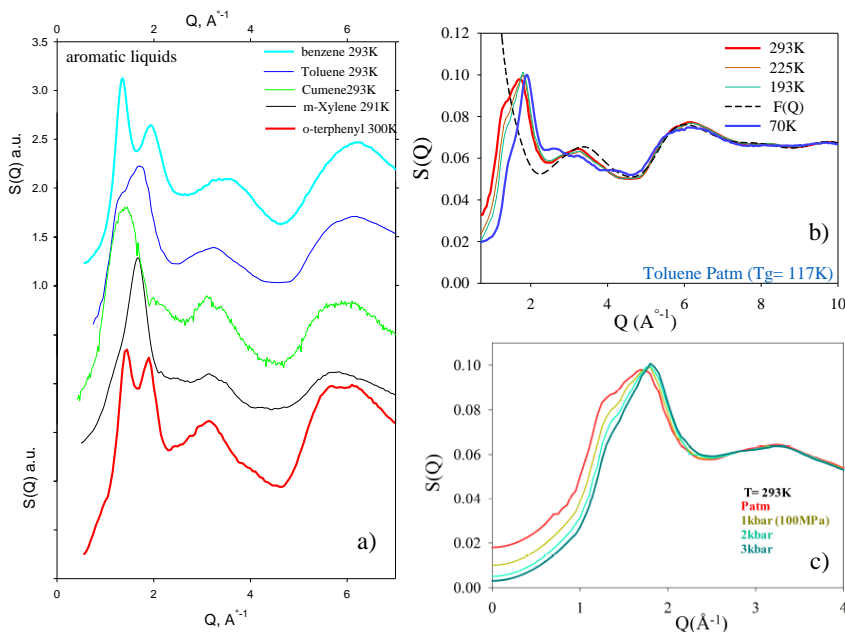


Figure 3. Static Structure factor of a serie of aromatic molecular liquids with increasing molecular weight as a function of the wave vector Q and its dependence on temperature, pressure and density, the systems are deuterated and measurements by elastic neutron scattering: a) benzene (only when confined in microemulsion T_g 120K, see also Figure 6, Toluene $T_g = 117\text{K}$, isopropyl benzene or cumene $T_g = 125\text{K}$, m-xylene $T_g = 125.5\text{K}$, ortho-terphenyl $T_g = 245\text{K}$); b) Temperature dependence of $S(Q)$ of toluene at atmospheric pressure from above T_m to below T_g ; in addition the form factor $F(Q)$ of the molecule is shown as a dashed line for its contribution at large Q 's; c) $S(Q)$ changes with pressure along an isotherm. All experiments have been performed on the diffractometer 7C2 at the Laboratoire Léon Brillouin, Saclay; details on the data traitement are given in [75].

involved in dynamical heterogeneities could be evaluated in the whole phase diagram [82]. The Figure 5 illustrates the different paths to the glass transition in a $P - T$ phase diagram (a) and how the dynamical properties evolve along different thermodynamical paths (b). It brings us to the question about the respective role of the various external control parameters, temperature T , pressure P and density (or volume V) in the viscous slowing down of glass forming liquids and polymers [83, 84]. One can observe from experiments performed at constant pressure that the role of temperature becomes more important in the super-Arrhenius regime as one approaches the glass transition than the density, which contribution is more significant at high temperatures [83].

Another way to modify the glass transition of a given system is to confine it at nanoscale. It was first considered as an extra trick to avoid crystallisation in liquids prone to crystallise: the use of microemulsions stable in time and in temperature allows the formation of glass with liquids such as benzene, CS_2 or CCl_4 [85]. Many experiments and simulations focussed on the effect of geometrical confinement on phase transitions, thermodynamics and dynamics of liquids. Restricted geometries have significant consequences on first order phase transitions (such as melting/freezing or solid-solid), but also in the glass formation [86–88]; phase transition

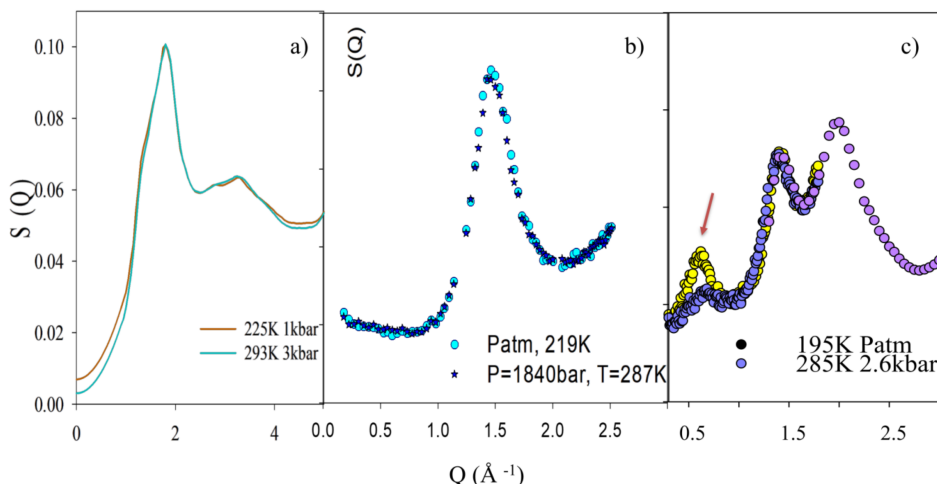


Figure 4. Static Structure factor along an isochore, T and P are indicated in the plot: a) a van der Waals liquid, toluene $\rho = 1.06\text{g/cm}^3$; b) a polymer, polubutadiene, $M_w=7000$, $\rho = 0.94\text{g/cm}^3$; c) an hydrogen bonded liquid m-fluoroaniline $\rho = 1.3\text{g/cm}^3$, here the arrow indicates the position of a prepeak due to the presence of H-bond induced clusters and its T-dependence associated with the strength of the H-bond [75].

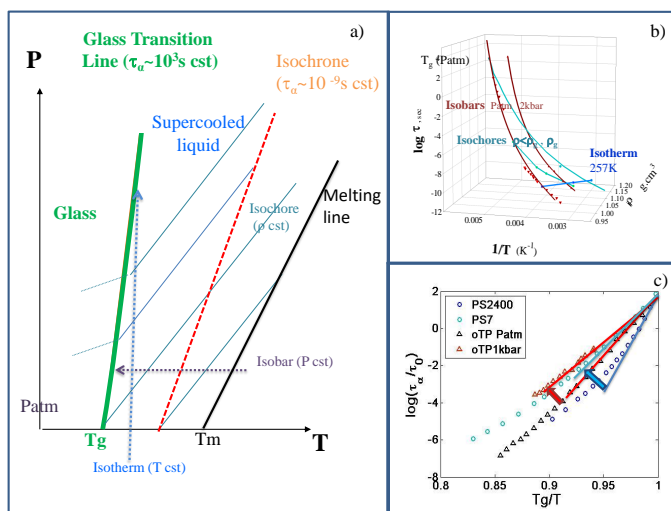


Figure 5. Supercooled and overcompressed liquid: a) Pressure-Temperature phase diagram with T_g line and melting line, illustrating the different thermodynamic paths, that can be used to obtain a glass; the T_g line is an “isochronic” line, i.e. a constant relaxation time line or isoviscous, other similar lines can be defined in the diagram for shorter relaxation times; b) 3D plot of the relaxation time of m-toluidine as a function of temperature and density with the different thermodynamical paths; c) relaxation time as a function of temperature rescaled by T_g for a molecular liquid (o-terphenyl) at two different isobars, Patm and 1kbar=100MPa (in red), and for a polymer (polystyrene) for two molecular weights M_w [63, 76–78] from N=7 monomers to 2400 monomers (in blue), the straight lines indicate how the (isobaric) fragility index is calculated and the arrows how the fragility evolves.

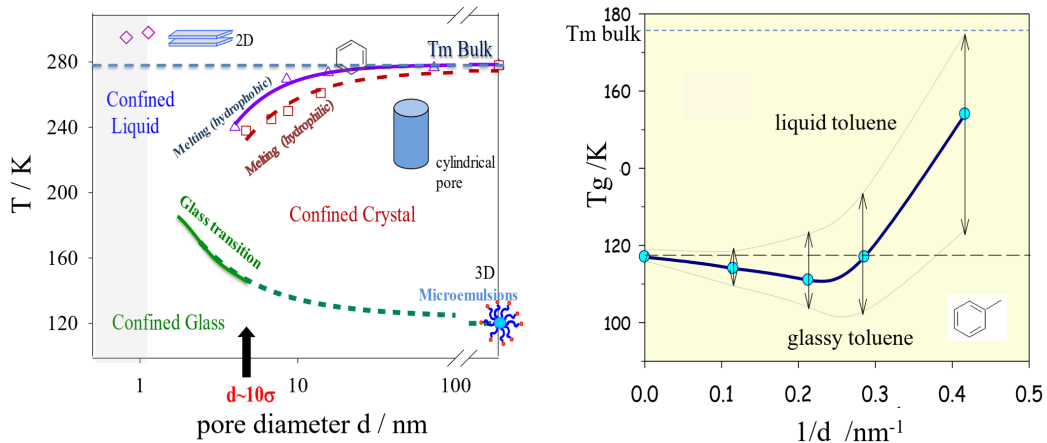


Figure 6. Temperature-Pore Diameter phase diagram of confined liquids: a) case of a liquid prone to crystallize, benzene C_6H_6 . The melting temperature is reduced according to the Gibbs Thomson law; in the smallest pores ($d < 10 \times$ molecular size), the confined liquid no longer crystallizes but rather exhibits a glass transition. A “pseudo” bulk T_g is obtained in quenched microemulsions of large pore size [73] around 200nm; b) Glass transition temperature of toluene versus the inverse of the pore diameter, the line is the calorimetric glass transition temperature defined at the maximum of the heat capacity derivative; the arrows represent the widths of the transition region increasing as the pore size decreases; the dashed lines refer to T_g and T_m of the bulk toluene [75].

pressures and temperatures are often shifted from the bulk values and new phases can appear due to surface forces. Thus another phase diagram $T - D$ can be considered where P in the previous one is replaced by the size of the confinement (D the pore diameter of the material), as illustrated in Figure 6. The study of the glass transition of confined liquids has been largely promoted on one hand by the idea that the geometrical restriction in the range 1 – 10 nm should compete with characteristic length scales responsible of the viscous slowing down, and, on the other hand, by the progress made in the synthesis of micro-mesoporous materials. Although the decrease of the melting temperature as the pore size decreases is robustly described by the Gibbs–Thomson equation, no satisfactory consensus has been found to predict experimentally the evolution of T_g with the pore size. Several experimental difficulties arise: the filling conditions, the existence of structural heterogeneities induced by the confinement, the distribution of the relaxation time between a solid wall and the center of the pore and finally, the ambiguous distinction between a crystalline nanograin and a glass. In order to conclude on finite size effects on the dynamics and on the quantification of a dynamic length, it is thus necessary to control concomitant effects due to the presence of an interface and the nature of the wall-liquid interaction; indeed T_g can decrease, increase or remain constant depending on these fluid-wall interactions and its consequences on the local organisation of the liquid. So far, the study of the glass transition under confinement does not allow the extraction of an intrinsic correlation length associated with the viscous slowing down approaching T_g , but it reveals the important role of matrix-adsorbate interactions and the competition between finite size effects and surface effects. However, thanks to the huge surface to volume ratio that nanopores offer, knowing how thermodynamics and dynamics of fluids are affected by confinement is of great importance for many applications and a better understanding in lubrication, adhesion, nanotribology, fabrication of other nano-materials etc. . .

3. Concept of Fragility

At the Blacksburg Workshop in 1984, in a published paper in 1985 [89], C.A. Angell proposed to compare and rank the liquids according to their fragility index m , i.e. their departure from an Arrhenius behavior; m characterises how quick in temperature the dynamics and the thermodynamics change above T_g . This index was first defined close to T_g as $m = \partial \log_{10}[\tau(T)/\tau_\infty] / \partial(T_g/T)|_{T_g}$, for liquids studied at normal pressure. (Note: fragile is distinct from brittle). In a logarithmic representation, the relaxation or the viscosity of different liquids are plotted as function of T_g/T , thus all converge at a single point $T_g/T = 1$ corresponding to the time of the chosen definition for the glass transition temperature, (see Figures 5 (c) and 7 (a)). The T_g scaling was already suggested several years before [90, 91], however when Angell introduced the fragility concept, he went a step further and claimed that “The temperature dependence of the average relaxation time as well as the detailed relaxation function seem to be closely connected with the nature of the intermediate range order. Thus, structural relaxation is the first of our glass science problems identified as involving the intermediate range order” [89], in an attempt to correlate dynamics with the thermodynamic behavior and local order. Accordingly, strong liquids are those with a low value of m and a pseudo tetrahedral structure, (about 16 for the strongest as silica, it is assume that $\log_{10}[\tau_\infty] = -14$), while the most fragile ones have a higher value, up to 200 for some high M_w polymers (polystyrene, $m = 139$; poly(vinyl chloride), $m = 191$). For molecular liquids it varies in a more narrow range from about 50 (glycerol, 53) to 90 (salol, $m = 73$, oTP, $m = 80$). Higher fragilities for molecular liquids can be found (sorbitol, decaline [92], etc.. above 130); however in all cases additional features such as mixtures of isomers, specific behavior of H-bond network or how the slope is calculated, might explain the high values. Differences in the temperature dependence of the relaxation time of liquids are sometimes quantified through other indices like the thermodynamic fragility [93–96] compared to the kinetic one, referring to the C_p jump or the change of the configurational entropy. The classification was extended to many different categories of systems: polymers, plastic crystals, and spin glasses [97–99]. It was also suggested to extend the classification by including the whole supercooled range, not only at T_g : the former index fragile *vs* non-fragile to measure how much the viscosity is Arrhenius-type at low temperature while the second one strong *vs* weak does the same around the melting point.

3.1. Isobaric versus Isochoric Fragility

We have learned from the experiments carried out under high pressure that to a large extent temperature is the driving parameter for viscous slowing down close to T_g , thus challenging a large number of existing models predicting a preponderant role of density via congestion effect and a decrease of the free volume. The contribution due to the density can be reduced to a single parameter, an effective activation energy $E_\infty(\rho)$ that is extracted from the data at high temperature, i.e. in a liquid and Arrhenius-like regime. Thus the simplest description of $\tau(T, \rho)$ can be reduced from $\tau_\alpha(\rho, T) = \tau_\alpha^\infty(\rho) \exp[E(\rho, T)/T]$ to $\tau_\alpha(\rho, T) = \tau_\alpha^\infty(\rho) \exp[E_\infty(\rho)/T]$. Accordingly, all isochoric data should collapse onto a master curve [44, 101, 111, 112]: the density scaling has been verified for many systems from molecular liquids to polymers and ionic liquids. It was confirmed by many groups using different probes, viscosity, dielectric spectroscopy, NMR, Neutron scattering [113–115]. Different functional forms are possible for describing the density dependence of $E_\infty(\rho)$, among them the power law dependence ρ^x , reminiscent of models of monodisperse soft spheres interacting through a power-law pair potential, seems to fit quite well the data. When only high viscosity or long relaxation times are available, without high temperature data to evaluate the effective activation energy $E_\infty(\rho)$ in absolute unit, then the scaling in terms of $e(\rho) \propto \rho^x$ works equally well as shown with polymers, ionic liquids [101].

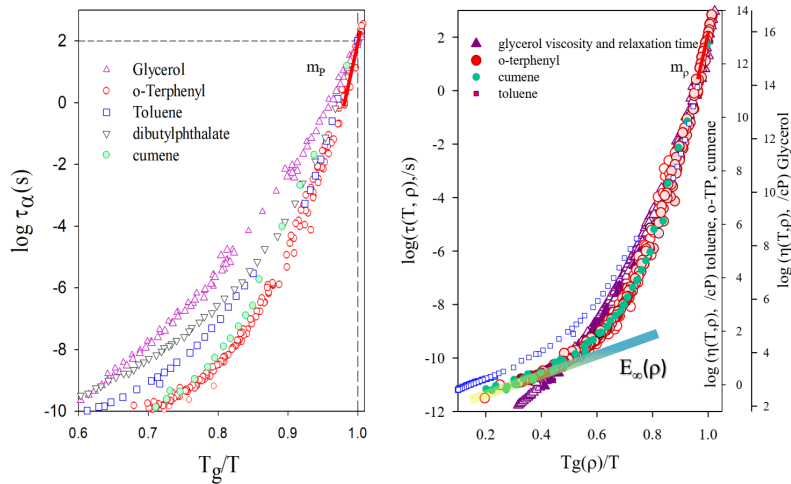


Figure 7. Dynamics of organic liquids and fragility. Left, the so-called Angell’s plot, relaxation time or viscosity of several molecular liquids at atmospheric pressure from slightly above the melting temperature to T_g defined at $\tau=200$ s, the red line at T_g defines the Angell “isobaric” fragility m_p of o-terphenyl. Right, relaxation time and viscosity of the same liquids data collected for all available (P, T) state points rescaled by $T_g(\rho)/T_g$; the red line indicated at $T_g(\rho)$ defines the “isochoric” fragility m_ρ independent of ρ ; the blue line represents a density dependent Arrhenius effective activation energy $E_\infty(\rho)$. Most data can be found in [100–110].

The exponent x of the power law varies from one liquid to another one, between less than 1 (sorbitol $x = 0.13$) to 8 (toluene), and is not always constant over a large pressure-density range. So far it was not checked for strong and inorganic liquids. The physical interpretation of this density scaling remains to be understood but new approaches such as the Isomorph theory tends to rationalise it [116]. In addition, one should stress that the Arrhenius behavior proposed for the high-T liquid has also no satisfactory theoretical explanation.

The density scaling has three major consequences. First, one can revisit the concept of fragility defined originally at constant pressure and introduce the isochoric fragility m_ρ :

$$m_\rho = \left. \frac{\partial \log(\tau_\alpha)}{\partial \left(\frac{T_g}{T}\right)} \right|_\rho \quad (T = T_g(\rho)),$$

here defined at the glass transition temperature at which τ_α has a given value at a given ρ . While the isobaric fragility includes the effects of temperature and density, the isochoric one is independent of density whatever is the density range explored. Thus, the isochoric fragility, i.e, the measure of the degree of super-Arrhenius behavior at constant density, must be taken as an intrinsic property of a given glassformer. The second consequence of the density scaling is a modified Angell plot as illustrated in Figure 7 (b). The Angell plot defining the isobaric fragility represents $\log(\tau_\alpha)$ versus the inverse scaled temperature T_g/T at constant (usually atmospheric) pressure in Figure 7 (a). Instead, one can plot $\log(\tau_\alpha)$ versus $T_g(\rho)/T$, where all T- ρ data of a specific liquid collapse and can be compared to another one (the scaling plot can be equivalently expressed as a function of X/X_g , where $X = e(\rho)/T$ is the scaling variable introduced above and X_g its value at the glass transition). The steepness of the $\log(\tau_\alpha)$ -vs- $T_g(\rho)/T$ curve is a measure of the intrinsic fragility of a system independent of ρ . One can notice that in the standard Angell plot, all the liquids have a different behavior and a different isobaric fragility, while in the

isochoric Angell plot, the liquids exhibit a similar isochoric fragility when the glass transition is approached. The third consequence of the existence of an intrinsic fragility only dependent on temperature rather than density illustrates a major difference with jamming process and colloidal suspensions.

Finally, the density scaling of the transport properties of supercooled liquids can be introduced in elastic or Adam–Gibbs approaches. In the latter case, while the dependence of the prefactor τ_0 remains negligible, the elementary activation energy expressed $A(\rho)$ scales as $E_\infty(\rho)$ and the configurational entropy $S_c(\rho, T)$ is only a function of the scaling variable $X = E_\infty(\rho)/T$, $S_c(\rho, T) = \Theta[E_\infty(\rho)/T]$. For practical purpose, the density scaling is useful in organizing or interpolating the experimental or simulated data obtained along different thermodynamic paths as soon as accurate equation of states are available.

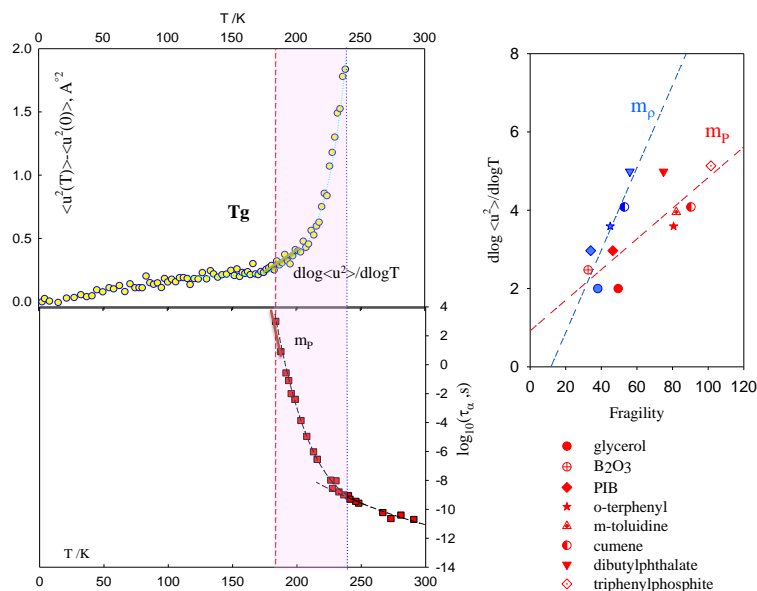


Figure 8. correlation between slow and fast dynamics of m-toluidine. Left top, mean square displacement (msd) $\langle u^2(T) \rangle$ at $4 ns$ as function of temperature measured by neutron scattering at atmospheric pressure; bottom, the corresponding structural relaxation time. Slightly above T_g defined at $\tau = 200s$, the pink area shows the respective change of the dynamics and of the msd. Right, correlation between the slope at T_g of the msd and isobaric in red and isochoric in blue fragility of different liquids given in the figure. Data from this work and [117].

3.2. Correlations between Slow and Fast dynamics

The Angell classification and the fragility index was intensively used in order to rationalise the rich phenomenology observed in supercooled liquids and glasses. A number of correlations have been proposed between fragility and other properties related to the glass transition to extract important features and improve models or theories [118–121]. The properties of liquids and polymers have been investigated mainly at atmospheric pressure and plotted as a function of the isobaric m_p , neglecting the possible specific dependence on temperature or density.

From the supercooled liquid side, m_p was correlated to the stretching exponent of the relaxation, the heat capacity jump or the decrease of the configurational entropy. From the glass side, properties are measured at very short times as for any solids and compared to the very slow dynamics above T_g . Among many properties, we can mention the relative intensity of the Boson peak observed by light or neutron scattering in the meV range, which appears directly related to the fragility of the system: the stronger the system, the greater the intensity. In this case the correlation with the isochoric fragility is comparable suggesting that the Boson peak intensity could be related to the effect of temperature on the dynamics and the super-Arrhenius behavior above T_g . Another proposed correlation involve the ratio of elastic to inelastic signal in the X-ray Brillouin spectra, also defined as the non-ergodicity factor. At variance to the previous case, the correlation becomes very poor when the isochoric fragility is considered [117, 122–124] and better related to density effects and the variation of $E_\infty(\rho)$ from one system to another one.

The correlations are critical to understanding the consequences of super-arrhenic behavior on the properties of glasses, establishing a link between solid and liquid models. Conversely, this raises the question of how properties probed on the pico-nano second time scale might determine slow processes observed over hours. A convincing example is given in Figure 8 for a molecular liquid, where the mean square displacement (msd) measured at a fixed time of 4 nanosecond and the structural relaxation evolve with temperature close to the glass transition: as shown, the larger MSD is related to the shorter relaxation time. It was first observed in 1992 by Buchenau and Zorn for Selenium [125], and generalise to all systems studied so far. Moreover the change in MSD just above T_g and the fragility, either m_p or m_ρ (Figure 8 right), is more pronounced for the most fragile systems, as predicted by elastic models. One should note that the correlation holds for MSD taken at the ns timescale, but fails when the msd is measured at the ps timescale and includes the vibrational contributions. Finally, one can always argue that correlation does not mean causality but a full understanding of the glass-transition must encompass both fast and slow dynamics.

4. Conclusion

In this short review, the properties of organic glass forming systems are presented in a non exhaustive way. Organic glasses constitute a very large and important category of materials with implications in many different fields where dynamical arrest takes place. The temperature range of their glass transition covers a large domain from the lowest T_g measured for a molecule at 56K to 400K and above for sugars and polymers; this range is much lower in temperature than that observed for inorganic materials, and still quite large compared to other systems experiencing a dynamical arrest. T_g changes with the chemical composition, the architecture of the system, the intermolecular interactions and evolves slightly with the mass. Some rules of thumb to locate T_g or define their ability to vitrify are discussed according to different thermodynamic paths or external constraints; the only relation resisting to the analysis of many liquids leads to a ratio $\frac{T_b}{T_g}$ always larger than 2, T_b being the boiling temperature at atmospheric pressure.

The most remarkable property of these liquids is how fast in temperature their viscosity or structural relaxation time increases as approaching T_g which is also described as a super-Arrhenius behavior. To characterize this behavior and rank the liquids of different strength, C.A. Angell introduced the concept of Fragility nearly 40 years ago. He proposed to classify liquids as fragile or strong in an Arrhenius plot with T_g scaling, the most fragile demonstrating the fastest changes in the dynamical properties. Originally considered only at atmospheric pressure, the study can be extended in a wider T-P range focussing on the specific contributions of temperature or density. At zeroth-order, the viscous slowing down is then shown to be best described as a thermally activated process, whose super-Arrhenius behavior is not primarily

driven by congestion effects due to lack of free volume. Moreover all $\tau(\rho, T)$ or $\eta(\rho, T)$ data collapse by placing the data on master curves that depend only on a single density- and species-dependent effective interaction energy (independent of T), $E_\infty(\rho)$, expressing the quantitative role of the density. This led to propose a modified version of the Angell plot, the isochoric Angell plot. However the most important consequence of the master curve obtained by scaling out the density dependence of the relaxation time is the introduction of an intrinsic property for each substance, the isochoric fragility m_ρ . All the correlations between the properties of the glass below T_g and the viscous slowing down just above T_g can be reconsidered by taking the isochoric fragility instead of the isobaric fragility; it is then a question of verifying in what way these properties are consecutive to the mechanisms put in place during cooling and the freezing produced at T_g , hoping for a more causal relationship.

The last considerations suggest that there are still two areas that may need further attention. First at very long relaxation times scrutinizing what happens between T_g and T_K , this has been proposed recently with highly stable glasses prepared by physical vapor deposition [126,127]. The procedure discovered by Ediger and his group provide new insights into properties of a possible ideal glass bypassing the kinetic problem of long aging. Such vapor deposition preparation techniques seem to be very promising, both in terms of understanding aging phenomena and in the preparation of new materials more thermodynamically and kinetically stable than those obtained through standard cooling rates. The second area is at higher temperatures, where the dynamics of glass-forming molecular liquids is well described by an Arrhenius temperature dependence with a sizable apparent activation energy $E_\infty(\rho)$. It raises the question of why the high temperature liquid dynamics of glassforming molecular systems is dominated by thermally activated processes (of several $k_B T$) and the possible location of a reference temperature (or energy) large compared to the melting temperature setting the scale for the activation energy.

Conflicts of interest

The author has no conflict of interest to declare.

References

- [1] C. A. Angell, "Formation of glasses from liquids and biopolymers", *Science* **267** (1995), no. 5206, p. 1924-1935.
- [2] C. A. Angell, J. M. Sore, E. J. Sore, "Glass Transition Temperatures for Simple Molecular Liquids and Their Binary Solutions", *J. Phys. Chem.* **82** (1978), no. 24, p. 2622--2629.
- [3] J. C. Dyre, "Colloquium: The glass transition and elastic models of glass-forming liquids", *Rev. Mod. Phys.* **78** (2006), no. 3, p. 952-972.
- [4] M. Descamps, A. Aumelas, S. Desprez, J. F. Willart, "The amorphous state of pharmaceuticals obtained or transformed by milling: Sub-Tg features and rejuvenation", *J. Non Cryst. Solids* **407** (2015), p. 72-80.
- [5] S. R. Forrest, M. E. Thompson, "Introduction: Organic Electronics and Optoelectronics", *Chem. Rev.* **107** (2007), no. 4, p. 923-925.
- [6] M. D. Ediger, P. Harrowell, "Perspective: Supercooled liquids and glasses", *J. Chem. Phys.* **137** (2012), article no. 080901.
- [7] A. Keiichiro, H. Suga, S. Syüzö, "Phase Changes in Crystalline and Glassy-Crystalline Cyclohexanol", *Bull. Chem. Soc. Jpn.* **41** (1968), no. 5, p. 1073-1087.
- [8] F. Affouard, M. Descamps, "Analogy of the slow dynamics between the supercooled liquid and supercooled plastic crystal states of difluorotetrachloroethane", *Phys. Rev. E* **72** (2005), no. 1, article no. 012501 (4 pages).
- [9] T. Hecksher, D. H. Torchinsky, C. Klieber, J. A. Johnson, J. C. Dyre, K. A. Nelson, "Toward broadband mechanical spectroscopy", *Proc. Natl. Acad. Sci. USA* **114** (2017), no. 33, p. 8710-8715.
- [10] M. H. Jensen, C. Gainaru, C. Alba-Simionesco, T. Hecksher, K. Niss, "Slow rheological mode in glycerol and glycerol-water mixtures", *Phys. Chem. Chem. Phys.* **20** (2018), no. 3, p. 1716-1723.
- [11] D. Kivelson, S. A. Kivelson, X. Zhao, Z. Nussinov, G. Tarjus, "A thermodynamic theory of supercooled liquids", *Physica A* **219** (1995), no. 1, p. 27-38.

- [12] W. Götze, L. Sjögren, "Relaxation processes in supercooled liquids", *Rep. Prog. Phys.* **55** (1992), no. 3, p. 241-376.
- [13] F. Fujara, B. Geil, H. Sillescu, G. Z. Fleischer, "Translational and rotational diffusion in supercooled orthoterphenyl close to the glass transition", *Z. Physik B - Condensed Matter* **88** (1992), p. 195-204.
- [14] M. T. Cicerone, M. D. Ediger, "Enhanced translation of probe molecules in supercooled o-terphenyl: Signature of spatially heterogeneous dynamics?", *J. Chem. Phys.* **104** (1996), p. 7210-7218.
- [15] P. Jacobsson, L. Börjesson, A. K. Hassan, L. M. Torell, "Reorientational motion of the NO₃⁻ ion through the liquid-glass transition in Ca_{0.4}K_{0.6}(NO₃)_{1.4} and Ca(NO₃)₂ + 8H₂O", *J. Non Cryst. Solids* **172-174** (1994), p. 161-166.
- [16] P. Luo, Y. Zhai, P. Falus, V. Garcia Sakai, M. Hartl, M. Kofu, K. Nakajima, F. Antonio, Y. Z., "Q-dependent collective relaxation dynamics of glass-forming liquid Ca_{0.4}K_{0.6}(NO₃)_{1.4} investigated by wide-angle neutron spin-echo", *Nat. Commun.* **13** (2022), no. 1, article no. 2092 (9 pages).
- [17] A. L. Greer, K. F. Kelton, S. Sastry (eds.), *Fragility of Glass-forming Liquids*, Texts and Readings in the Physical Sciences (TRIPS), vol. 13, Hindustan Book Agency, 2014, Collection of article accompagnies the Symposium on Fragility held at JNCASR, Bengaluru, India, 2014.
- [18] M. D. Ediger, C. A. Angell, S. R. Nagel, "Supercooled liquids and glasses", *J. Phys. Chem.* **100** (1996), no. 31, p. 13200-13212.
- [19] W. Kauzmann, "The Nature of the Glassy State and the Behavior of Liquids at Low Temperatures", *Chem. Rev.* **43** (1948), no. 2, p. 219-256.
- [20] J. H. Gibbs, E. A. DiMarzio, "Nature of the glass transition and the glassy state", *J. Chem. Phys.* **28** (1958), p. 373-383.
- [21] G. Adam, J. H. Gibbs, "On the temperature dependence of cooperative relaxation properties in glass-forming liquids", *J. Chem. Phys.* **43** (1965), p. 139-146.
- [22] S. A. Kivelson, G. Tarjus, "In search of a theory of supercooled liquids", *Nature Mater.* **7** (2008), p. 831-833.
- [23] L. Berthier, G. Biroli, "Theoretical perspective on the glass transition and amorphous materials", *Rev. Mod. Phys.* **83** (2011), no. 2, p. 587-645.
- [24] V. Lubchenko, P. G. Wolynes, "Theory of Structural Glasses and Supercooled Liquids", *Annu. Rev. Phys. Chem.* **58** (2007), p. 235-266.
- [25] J. D. Stevenson, J. Schmalian, P. G. Wolynes, "The shapes of cooperatively rearranging regions in glass-forming liquids", *Nature Phys.* (2006), p. 268-274.
- [26] G. Tarjus, "An overview of the theories of the glass transition", in *Dynamical Heterogeneities and Glasses* (L. Berthier, G. Biroli, J.-P. Bouchaud, L. Cipelletti, W. van Saarloos, eds.), International Series of Monographs on Physics, vol. 150, Oxford University Press, 2011, p. 152-203.
- [27] R. Richert, N. Israeloff, C. Alba-Simionesco, F. Ladieu, D. L'Hôte, "Experimental Approaches to Heterogeneous Dynamics", in *Dynamical Heterogeneities in Glasses, Colloids and Granular Materials*, (L. Berthier, G. Biroli, J. P. Bouchaud, eds.), International Series of Monographs on Physics, vol. 150, Oxford University Press, 2011, p. 152-202.
- [28] L. Berthier, G. Biroli, J.-P. Bouchaud, L. Cipelletti, D. El Masri, D. L'Hôte, F. Ladieu, M. Pierno, "Direct experimental evidence of a growing length scale accompaying the glass transition", *Science* **310** (2005), no. 5755, p. 1797-1800.
- [29] C. Dalle-Ferrier, C. Thibierge, C. Alba-Simionesco, L. Berthier, G. Biroli, J.-P. Bouchaud, F. Ladieu, D. L'Hôte, G. Tarjus, "Spatial correlations in the dynamics of glassforming liquids: Experimental determination of their temperature dependence", *Phys. Rev. E* **76** (2007), no. 4, article no. 041510.
- [30] L. Berthier, G. Biroli, J.-P. Bouchaud, G. Tarjus, "Can the glass transition be explained without a growing static length scale?", *J. Chem. Phys.* **150** (2019), article no. 094501.
- [31] W. A. Phillips, "Two-level states in glasses", *Rep. Prog. Phys.* **50** (1987), no. 12, p. 1657.
- [32] R. C. Zeller, R. O. Pohl, "Thermal conductivity and specific heat of noncrystalline solids", *Phys. Rev. B* **4** (1971), no. 6, p. 2029-2041.
- [33] D. A. Parshin, H. R. Schober, V. L. Gurevich, "Vibrational instability, two-level systems, and the boson peak in glasses", *Phys. Rev. B* **76** (2007), no. 6, article no. 064206 (16 pages).
- [34] W. Schirmacher, G. Ruocco, T. Scopigno, "Acoustic attenuation in glasses and its relation with the Boson peak", *Phys. Rev. Lett.* **98** (2007), no. 2, article no. 025501 (4 pages).
- [35] F. Leonforte, A. Tanguy, J. P. Wittmer, J.-L. Barrat, "Continuum limit of amorphous elastic bodies II: Linear response to a point source force", *Phys. Rev. B* **70** (2004), no. 1.
- [36] F. Casas, C. Alba-Simionesco, H. Montes, F. Lequeux, "Length-Scale of Glassy Polymer Plastic Flow: A Neutron Scattering Study", *Macromolecules* **41** (2008), no. 3, p. 860-865.
- [37] L. Hong, V. N. Novikov, A. P. Sokolov, "Dynamic heterogeneities, boson peak, and activation volume in glass-forming liquids", *Phys. Rev. E* **83** (2011), no. 6, article no. 061508 (10 pages).
- [38] D. Fragiadakis, R. Casalini, C. M. Roland, "Comparing dynamic correlation lengths from an approximation to the four-point dynamic susceptibility and from the picosecond vibrational dynamics", *Phys. Rev. E* **84** (2011), no. 4, article no. 042501 (4 pages).
- [39] M. H. Cohen, D. Turnbull, "Molecular transport in liquids and glasses", *J. Chem. Phys.* **31** (1959), p. 1164-1169.
- [40] D. Chandler, J. P. Garrahan, "Dynamics on the way to forming glass: Bubbles in space-time", *Annu. Rev. Phys. Chem.* **61** (2010), p. 191-217.

- [41] C. P. Royall, F. Turci, T. Speck, "Dynamical phase transitions and their relation to structural and thermodynamic aspects of glass physics", *J. Chem. Phys.* **153** (2020), article no. 090901.
- [42] G. Kapteijns, D. Richard, E. Bouchbinder, T. B. Schröder, J. C. Dyre, E. Lerner, "Does mesoscopic elasticity control viscous slowing down in glassforming liquids?", *J. Chem. Phys.* **155** (2021), article no. 074502.
- [43] J. C. Dyre, N. B. Olsen, T. Christensen, "Local elastic expansion model for viscous-flow activation energies of glass-forming molecular liquids", *Phys. Rev. B* **53** (1996), no. 5, p. 2171-2174.
- [44] C. Alba-Simionesco, D. Kivelson, G. Tarjus, "Thermodynamic properties of liquid toluene", *J. Phys. Chem.* **92** (1988), p. 487-489.
- [45] H. Vogel, "Das Temperaturabhängigkeitsgesetz der Viskosität von Flüssigkeiten", *Phys. Zeit.* **22** (1921), p. 645-646.
- [46] G. S. Fulcher, "Analysis of recent measurements of the viscosity of glasses", *J. Am. Ceram. Soc.* **8** (1925), p. 339-355.
- [47] G. Tammann, "Glasses as supercooled liquids", *J. Soc. Glass Technol.* **9** (1925), p. 166-185.
- [48] H. Bässler, "Viscous flow in supercooled liquids analyzed in terms of transport theory for random media with energetic disorder", *Phys. Rev. Lett.* **58** (1987), no. 8, p. 767-770.
- [49] T. Hecksher, A. Nielsen, N. Boye Olsen, J. C. Dyre, "Little evidence for dynamic divergences in ultraviscous molecular liquids", *Nature Phys.* **4** (2008), p. 737-741.
- [50] J. C. Mauro, Y. Yue, A. J. Ellison, P. K. Gupta, D. C. Allan, "Viscosity of glass-forming liquids", *Proc. Natl. Acad. Sci. USA* **106** (2009), no. 47, p. 19780-19784.
- [51] V. N. Novikov, A. P. Sokolov, "Qualitative change in structural dynamics of some glass-forming systems", *Phys. Rev. E* **92** (2015), no. 6, article no. 062304 (8 pages).
- [52] S. Tatsumi, S. Aso, O. Yamamuro, "Thermodynamic study of simple molecular glasses: universal features in their heat capacity and the size of the cooperatively rearranging regions", *Phys. Rev. Lett.* **109** (2012), no. 4, article no. 045701 (5 pages).
- [53] A. Simperler, A. Kornherr, R. Chopra, P. A. Bonnet, W. Jones, W. D. S. Motherwell, G. Zifferer, "Glass Transition Temperature of Glucose, Sucrose, and Trehalose: An Experimental and in Silico Study", *J. Phys. Chem. B* **110** (2006), no. 39, p. 19678-19684.
- [54] Y. Roos, "Melting and glass transitions of low molecular weight carbohydrates", *Carbohydr. Res.* **238** (1993), p. 39-48.
- [55] S. Linnenkugel, A. H. J. Paterson, L. M. Huffman, J. E. Bronlund, "Prediction of the effect of water on the glass transition temperature of low molecular weight and polysaccharide mixtures", *Food Hydrocolloids* **128** (2022), article no. 107573.
- [56] K. D. Roe, T. P. Labuza, "Glass Transition and Crystallization of Amorphous Trehalose-sucrose Mixtures", *Int. J. Food Prop.* **8** (2005), no. 3, p. 559-574.
- [57] S. Linnenkugel, A. H. J. Paterson, L. M. Huffman, J. E. Bronlund, "Prediction of the effect of water on the glass transition temperature of low molecular weight and polysaccharide mixtures", *Food Hydrocolloids* **128** (2022), article no. 107573.
- [58] J. D. Ferry, *Viscoelastic Properties of Polymers*, 3rd ed., John Wiley & Sons, 1980.
- [59] B. Frick, D. Richter, "The microscopic basis of the GT in polymers from neutron scattering studies", *Science* **267** (1995), no. 5206, p. 1939-1945.
- [60] S. Napolitano, E. Glynos, N. B. Tito, "Glass transition of polymers in bulk, confined geometries, and near interfaces", *Rep. Prog. Phys.* **80** (2017), article no. 036602.
- [61] R. Xie, A. R. Weisen, Y. Lee, M. A. Aplan, A. M. Fenton, A. E. Masucci, F. Kempe, M. Sommer, C. W. Pester, R. H. Colby, E. D. Gomez, "Glass transition temperature from the chemical structure of conjugated polymers", *Nat. Commun.* **11** (2020), article no. 893 (8 pages).
- [62] Y. Ding, V. N. Novikov, A. P. Sokolov, C. Dalle-Ferrier, C. Alba-Simionesco, B. Frick, "Influence of Molecular Weight on Fast Dynamics and Fragility of Polymer", *Macromolecules* **37** (2004), no. 24, p. 9264-9272.
- [63] C. Dalle-Ferrier, K. Niss, A. P. Sokolov, B. Frick, J. Serrano, C. Alba-Simionesco, "The role of chain length in nonergodicity factor and fragility of polymers", *Macromolecules* **43** (2010), no. 21, p. 8977-8984.
- [64] G. B. McKenna, S. L. Simon, "50th Anniversary Perspective: Challenges in the Dynamics and Kinetics of Glass-Forming Polymers", *Macromolecules* **50** (2017), no. 17, p. 6333-6361.
- [65] W. Ping, D. Paraska, R. Baker, P. Harrowell, C. A. Angell, "Molecular Engineering of the Glass Transition: Glass-Forming Ability across a Homologous Series of Cyclic Stilbenes", *J. Phys. Chem. B* **115** (2011), no. 16, p. 4696-4702.
- [66] W. Doster, A. Bachleitner, R. Dunau, M. Hiebi, E. Luscher, "Thermal properties of water in myoglobin crystals and solutions at subzero temperatures", *Biophys. J.* **50** (1986), no. 2, p. 213-219.
- [67] H. Frauenfelder, S. G. Sligar, P. C. Wolynes, "The energy landscapes and motions of proteins Science", *Science* **254** (1991), no. 5038, p. 1598-1603.
- [68] B. F. Rasmussen, A. M. Stock, D. Ringe, G. A. Petsko, "Crystalline ribonuclease A loses function below the dynamical transition at 220 K", *Nature* **357** (1992), p. 423-424.
- [69] J. Smith, K. Kuczera, M. Karplus, "Dynamics of myoglobin: Comparison of simulation results with neutron scattering spectra", *Proc. Natl. Acad. Sci. USA* **87** (1990), no. 4, p. 1601-1605.

- [70] D. Turnbull, M. H. Cohen, "Concerning reconstructive transformation and formation of glass", *J. Chem. Phys.* **29** (1958), p. 1049-1054.
- [71] C. Alba-Simionesco, J. Fan, C. A. Angell, "Thermodynamic aspects of the glass transition phenomenon. Molecular liquids with variable interactions", *J. Chem. Phys.* **110** (1999), p. 5262-5272.
- [72] L.-M. Wang, R. Richert, "Glass Transition Dynamics and Boiling Temperatures of Molecular Liquids and Their Isomers", *J. Phys. Chem. B* **111** (2007), no. 12, p. 3201-3207.
- [73] G. Dosseh, Y. Xia, C. Alba-Simionesco, "Cyclohexane and benzene confined in MCM-41 and SBA-15: Confinement effects on freezing and melting", *J. Phys. Chem. B* **107** (2003), no. 26, p. 6445-6453.
- [74] M. D. Ediger, P. Harrowell, L. Yu, "Crystal growth kinetics exhibit a fragility-dependent decoupling from viscosity", *J. Chem. Phys.* **128** (2008), article no. 034709 (6 pages).
- [75] M. Denis, C. Alba-Simionesco, "Hydrogen-bond-induced clustering in the fragile glassforming liquid *m*-toluidine: experiments and simulations", *J. Chem. Phys.* **109** (1998), p. 8494-8503.
- [76] J. Hintermeyer, A. Herrmann, R. Kahlau, C. Goiceanu, E. Rossler, "Molecular Weight Dependence of Glassy Dynamics in Linear Polymers Revisited", *Macromolecules* **41** (2008), no. 23, p. 9335-9344.
- [77] Y. Ding, V. N. Novikov, A. P. Sokolov, C. Dalle-Ferrier, C. Alba-Simionesco, B. Frick, "Influence of Molecular Weight on Fast Dynamics and Fragility of Polymers", *Macromolecules* **37** (2004), no. 24, p. 9264-9272.
- [78] C. M. Roland, R. Casalini, "Temperature dependence of local segmental motion in polystyrene and its variation with molecular weight", *J. Chem. Phys.* **119** (2003), p. 1838-1842.
- [79] A. Cailliaux, C. Alba-Simionesco, B. Frick, L. Willner, I. Goncharenko, "Local structure and glass transition of polybutadiene up to 4 GPa", *Phys. Rev. E* **67** (2003), no. 1, article no. 010802 (4 pages).
- [80] C. Alba-Simionesco, "Isothermal glass transitions in supercooled and overcompressed liquids", *J. Chem. Phys.* **100** (1994), p. 2250-2257.
- [81] B. Frick, C. Alba-Simionesco, K. H. Andersen, L. Willner, "Influence of Density and Temperature on the Microscopic Structure and the Segmental Relaxation of Polybutadiene", *Phys. Rev. E* **67** (2003), no. 5, article no. 51801 (15 pages).
- [82] C. Alba-Simionesco, C. Dalle-Ferrier, G. Tarjus, "Effect of pressure on the number of dynamically correlated molecules when approaching the glass transition", in *4th International Symposium on Slow Dynamics in Complex Systems*, AIP Conference Proceedings, vol. 1518, American Institute of Physics, 2013, p. 527-535.
- [83] M. L. Ferrer, C. Lawrence, B. G. Demirjian, D. Kivelson, G. Tarjus, C. Alba-Simionesco, "Supercooled liquids and the glass transition: Temperature as the control variable", *J. Chem. Phys.* **109** (1998), p. 8010-8015.
- [84] C. Alba-Simionesco, D. Kivelson, G. Tarjus, "Temperature, density, and pressure dependence of relaxation times in supercooled liquids", *J. Chem. Phys.* **116** (2002), p. 5033-5038.
- [85] J. Dubochet, C. M. Alba, D. R. MacFarlane, C. A. Angell, R. K. Kadiyala, M. Adrian, J. Teixeira, "Glass-forming microemulsions: vitrification of simple liquids and electron microscope probing of droplet-packing modes", *J. Phys. Chem.* **88** (1984), no. 26, p. 6727-6732.
- [86] M. Alcoutlabi, G. B. McKenna, "Effect of confinement on material behaviour at the nanometre size scale", *J. Phys.: Condens. Matter* **17** (2005), no. 15, p. R461-R524.
- [87] C. Alba-Simionesco, B. Coasne, G. Dosseh, G. Dudziak, K. E. Gubbins, R. Radhakrishnan, M. Sliwiska-Bartkowiak, "Effects of confinement on freezing and melting", *J. Phys.: Condens. Matter* **18** (2006), no. 6, p. R15-R68.
- [88] G. Dosseh, C. Le Quellec, N. Brodie-linder, C. Alba-Simionesco, W. Haeussler, P. Levitz, "Fluid-wall interactions effects on the dynamical properties of confined σ TP", *J. Non Cryst. Solids* **352** (2006), no. 42-49, p. 4964-4968.
- [89] C. A. Angell, "Spectroscopy simulation and scattering, and the medium range order problem in glass", *J. Non-Cryst. Solids* **73** (1985), no. 1-3, p. 1-17.
- [90] W. T. Laughlin, D. R. Uhlmann, "Viscous flow in simple organic liquids", *J. Phys. Chem.* **76** (1972), no. 16, p. 2317-2325.
- [91] D. L. Sidebottom, "Fifty years of fragility: A view from the cheap seats", *J. Non-Cryst. Solids* **524** (2019), article no. 119641.
- [92] L.-M. Wang, C. A. Angell, R. Ranko, "Fragility and thermodynamics in nonpolymeric glass-forming liquids", *J. Chem. Phys.* **125** (2006), article no. 074505.
- [93] I. Kaori, T. Moynihan Cornelius, C. A. Angell, "Thermodynamic determination of fragility in liquids and a fragile-to-strong liquid transition in water", *Nature* **398** (1999), p. 492-495.
- [94] M. L. Ferrer, H. Sakai, D. Kivelson, C. Alba-Simionesco, "Extension of the Angell fragility concept", *J. Phys. Chem. B* **103** (1999), no. 20, p. 4191-4196.
- [95] W. Li-Min, V. Velikov, C. A. Angell, "Direct determination of kinetic fragility indices of glassforming liquids by differential scanning calorimetry: Kinetic versus thermodynamic fragilities", *J. Chem. Phys.* **117** (2002), no. 22, p. 10184-10192.
- [96] J. C. Dyre, N. B. Olsen, T. Christensen, "Local elastic expansion model for viscous low activation energies of glass-forming molecular liquids", *Phys. Rev. B* **53** (1996), no. 5, p. 2171-2174.
- [97] J. Souletie, D. Bertrand, "Glasses and spin glasses: a parallel", *J. Phys. I* **1** (1991), no. 11, p. 1627-1637.

- [98] D. Huang, G. B. McKenna, "New insights into the fragility dilemma in liquids", *J. Chem. Phys.* **114** (2001), no. 13, p. 5621-5630.
- [99] S. Lansab, P. Münzner, Z. Herbert, R. Böhmer, "Deuteron nuclear magnetic resonance and dielectric studies of molecular reorientation and charge transport in succinonitrile-glutaronitrile plastic crystals", *J. Non Cryst. Solids* **14** (2022), article no. 100097.
- [100] B. Schmidtke, N. Petzold, R. Kahlau, E. A. Rössler, "Reorientational dynamics in molecular liquids as revealed by dynamic light scattering: From boiling point to glass transition temperature", *J. Chem. Phys.* **139** (2013), article no. 084504.
- [101] C. Alba-Simionesco, G. Tarjus, "A perspective on the fragility of glass-forming liquids", *Journal of Non-Crystalline Solids: X* **14** (2022), article no. 100100.
- [102] E. Rossler, H. Sillescu, "2H NMR Study of supercooled toluene", *Chem. Phys. Lett.* **112** (1984), p. 94-98.
- [103] L. Ter Minassian, K. Bouzar, C. Alba-Simionesco, "2H NMR Study of supercooled toluene", *Chem. Phys. Lett.* **112** (1984), p. 94-98.
- [104] G. Fytas, C. H. Wang, D. Lilje, T. Dorfmueller, "Homodyne light beating spectroscopy of o-terphenyl in the supercooled liquid state", *J. Chem. Phys.* **75** (1981), p. 4247-4255.
- [105] M. Naoki, S. Koeda, "Pressure-volume-temperature relations of liquid, crystal, and glass of o-terphenyl: excess amorphous entropies, and factors determining molecular mobility", *J. Phys. Chem.* **93** (1989), p. 948-955.
- [106] K. U. Schug, H. E. King Jr., R. Böhmer, "Fragility under pressure: Diamond anvil cell viscometry of ortho-terphenyl and salol", *J. Chem. Phys.* **109** (1998), p. 1472-1477.
- [107] G. P. Johari, E. Whalley, "Dielectric Properties of Glycerol in the Range 0.1 105 Hz, 218357 K, 0 – 53 kbar", *Faraday Symp. Chem. Soc.* **6** (1973), p. 23-41.
- [108] R. L. Cook, H. E. J. King, C. A. Herbst, D. R. Herschbach, "Pressure and temperature dependent viscosity of two glass forming liquids: Glycerol and dibutyl phthalate", *J. Chem. Phys.* **100** (1994), p. 5178-5189.
- [109] A. J. Barlow, J. Lamb, A. J. Matheson, "Glass Transition Temperature and Density Scaling in Cumene at Very High Pressure", *Proc. R. Soc. A* **292** (1966), p. 322-342.
- [110] G. Li, H. E. J. King, W. F. Oliver, C. A. Herbst, H. Z. Cummins, "Pressure and Temperature Dependence of Glass-Transition Dynamics in a "Fragile" Glass Former", *Phys. Rev. Lett.* **74** (1995), p. 2280-2283.
- [111] G. Tarjus, D. Kivelson, S. Mossa, C. Alba-Simionesco, "Disentangling density and temperature effects in the viscous slowing down of glassforming liquids", *J. Chem. Phys.* **120** (2004), p. 6135-6141.
- [112] C. Alba-Simionesco, A. Cailliaux-Chauty, A. Alegria, G. Tarjus, "Scaling out the density dependence of the α relaxation in glassforming polymers", *Eur. Phys. Lett.* **68** (2004), no. 1, p. 58-64.
- [113] C. M. Roland, S. Hensel-Bielowka, M. Paluch, R. Casalini, "Supercooled dynamics of glass-forming liquids and polymers under hydrostatic pressure", *Rep. Prog. Phys.* **68** (2005), p. 1405-1478.
- [114] M. Paluch, S. Haracz, A. Grzybowski, M. Mierzwa, J. Pionteck, A. Rivera-Calzada, C. Leon, "A Relationship between Intermolecular Potential, Thermodynamics, and Dynamic Scaling for a Supercooled Ionic Liquid", *J. Phys. Chem. Lett.* **1** (2010), no. 6, p. 987-992.
- [115] H. Wase Hansen, F. Lundin, K. Adrjanowicz, B. Frick, A. Matic, K. Niss, "Density scaling of structure and dynamics of an ionic liquid", *Phys. Chem. Chem. Phys.* **22** (2020), p. 14169-14176.
- [116] J. C. Dyre, "Isomorphs, hidden scale invariance, and quasiuniversality", *Phys. Rev. E* **88** (2013), no. 4, article no. 042139 (9 pages).
- [117] K. Niss, C. Alba-Simionesco, "Effects of Density and Temperature effects on correlations between fragility and glassy properties", *Phys. Rev. B* **74** (2006), no. 2, article no. 024205 (7 pages).
- [118] A. P. Sokolov, E. A. Rössler, A. Kisliuk, D. Quitmann, "Dynamics of strong and fragile glass formers: Differences and correlation with low-temperature properties", *Phys. Rev. Lett.* **71** (1993), no. 13, p. 2062-2065.
- [119] T. Scopigno, G. Ruocco, F. Sette, G. Monaco, "Is the fragility of a liquid embedded in the properties of its glass?", *Science* **302** (2003), no. 5646, p. 849-852.
- [120] V. N. Novikov, A. P. Sokolov, "Poisson's ratio and the fragility of glass-forming liquids", *Nature* **431** (2004), p. 961–963.
- [121] A. Widmer-Cooper, P. Harrowell, "Predicting the Long-Time Dynamic Heterogeneity in a Supercooled Liquid on the Basis of Short-Time Heterogeneities", *Phys. Rev. Lett.* **96** (2006), no. 18, article no. 185701 (4 pages).
- [122] K. Niss, C. Dalle-Ferrier, V. M. Giordano, G. Monaco, B. Frick, C. Alba-Simionesco, "Glassy properties and viscous slowing down: An analysis of the correlation between nonergodicity factor and fragility", *J. Chem. Phys.* **129** (2008), no. 19, article no. 194513.
- [123] K. Niss, C. Dalle-Ferrier, G. Tarjus, C. Alba-Simionesco, "On the correlation between fragility and stretching in glass-forming liquids", *J. Phys.: Condens. Matter* **24** (2012), no. 5, article no. 059501.
- [124] K. Niss, C. Dalle-Ferrier, B. Frick, D. Russo, J. C. Dyre, C. Alba-Simionesco, "Connection between slow and fast dynamics of molecular liquids around the glass transition", *Phys. Rev. E* **82** (2010), no. 2, article no. 021508 (8 pages).
- [125] U. Buchenau, R. Zorn, "A Relation Between Fast and Slow Motions in Glassy and Liquid Selenium", *Eur. Phys. Lett.* **18** (1992), no. 6, p. 523-528.

- [126] S. F. Swallen, K. L. Kearns, M. K. Mapes, Y. S. Kim, R. J. McMahon, M. D. Ediger, T. Wu, L. Yu, S. Satija, "Organic glasses with exceptional thermodynamic and kinetic stability", *Science* **315** (2007), no. 5810, p. 353-356.
- [127] M. D. Ediger, "Perspective: Highly stable vapor-deposited glasses", *J. Chem. Phys.* **147** (2017), no. 21, article no. 210901.